

BS EN 15860:2010



BSI Standards Publication

Plastics — Thermoplastic semi-finished products for machining — Requirements and test methods

NO COPYING WITHOUT BSI PERMISSION EXCEPT AS PERMITTED BY COPYRIGHT LAW

raising standards worldwide™

Provided by IHS
No reproduction or networking permitted without license from IHS

Not for Resale



National foreword

This British Standard is the UK implementation of EN 15860:2010.

The UK participation in its preparation was entrusted to Technical Committee PRI/82, Thermoplastic materials.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© BSI 2010

ISBN 978 0 580 63638 7

ICS 83.080.20

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 July 2010

Amendments issued since publication

Date	Text affected
------	---------------

EUROPEAN STANDARD
NORME EUROPÉENNE
EUROPÄISCHE NORM

EN 15860

June 2010

ICS 83.080.20

English Version

Plastics - Thermoplastic semi-finished products for machining - Requirements and test methods

Plastiques - Produits semi-finis thermoplastiques pour
usinage - Exigences et méthodes d'essai

Kunststoffe - Thermoplastische Halbzeuge für die
spanende Verarbeitung - Anforderungen und Prüfmethoden

This European Standard was approved by CEN on 19 May 2010.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: Avenue Marnix 17, B-1000 Brussels

© 2010 CEN All rights of exploitation in any form and by any means reserved
worldwide for CEN national Members.

Ref. No. EN 15860:2010: E

Contents

Page

Foreword	4
1 Scope.....	5
2 Normative references.....	5
3 Terms and definitions	6
4 Materials	6
5 Requirements.....	8
5.1 As-delivered condition.....	8
5.2 Surface appearance.....	8
5.3 Dimensions and tolerances for rods	8
5.3.1 Diameter	8
5.3.2 Length.....	10
5.3.3 Roundness	10
5.3.4 Straightness.....	11
5.4 Dimensions and tolerances for hollow bars.....	12
5.4.1 Diameters	12
5.4.2 Length.....	14
5.4.3 Roundness	14
5.4.4 Straightness.....	14
5.4.5 Concentricity.....	15
5.5 Dimensions and tolerances for panels/plates.....	16
5.5.1 Thickness	16
5.5.2 Length and width.....	17
5.5.3 Straightness.....	17
5.6 Properties.....	20
5.6.1 Physical properties.....	20
5.6.2 Dimensional stability after heat treatment.....	24
5.6.3 Physiological behaviour	26
6 Test methods	26
6.1 Test conditions	26
6.2 Sampling size.....	26
6.3 Test specimen preparation.....	26
6.3.1 Mechanical properties.....	26
6.3.2 Density.....	28
6.3.3 Melt volume-flow rate, viscosity number, melting temperature/glass transition temperature.....	28
6.3.4 Dimensional stability after heat treatment.....	28
6.4 As-delivered condition.....	29
6.5 Surface appearance.....	29
6.6 Accuracy of the dimension measuring instruments.....	29
6.7 Density.....	29
6.8 Tensile stress at yield and elongation at break.....	29
6.9 Tensile modulus of elasticity	30
6.10 Vicat softening temperature.....	30
6.11 Melt volume-flow rate (MVR)	30
6.12 Melting temperature/glass transition temperature.....	31
6.13 Viscosity number.....	31
6.14 Dimensional stability after heat treatment.....	31
6.15 Preparation of test results.....	35

7	Designation	35
7.1	Rods.....	35
7.2	Hollow bars	35
7.3	Panels/plates.....	36
8	Marking.....	36
Annex A (normative) Procedure for the determination of microporosity in semi-finished products		37
Annex B (normative) Tables for the conversion of deflection values (straightness).....		41
Annex C (informative) Examples of calculation of dimensional stability after heat treatment.....		44
C.1	Rods.....	44
C.2	Hollow bars	44
C.3	Panels/plates.....	45
Bibliography.....		46

Foreword

This document (EN 15860:2010) has been prepared by Technical Committee CEN/TC 249 "Plastics", the secretariat of which is held by NBN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by December 2010, and conflicting national standards shall be withdrawn at the latest by December 2010.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights other than those identified above. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and the United Kingdom.

1 Scope

This European Standard specifies the requirements and associated test methods that apply to semi-finished products such as rods, hollow bars and plates made from thermoplastic materials. These semi-finished products are used predominantly for the manufacture of finished parts by means of machining.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN ISO 291:2008, Plastics — Standard atmospheres for conditioning and testing (ISO 291:2008)

EN ISO 306, Plastics — Thermoplastic materials — Determination of Vicat softening temperature (VST) (ISO 306:2004)

EN ISO 307, Plastics — Polyamides — Determination of viscosity number (ISO 307:2007)

EN ISO 527-1, Plastics — Determination of tensile properties — Part 1: General principles (ISO 527-1:1993 including Corr. 1:1994)

EN ISO 527-2:1996, Plastics — Determination of tensile properties — Part 2: Test conditions for moulding and extrusion plastics (ISO 527-2:1993 including Corr. 1:1994)

EN ISO 1043-1:2001, Plastics — Symbols and abbreviated terms — Part 1: Basic polymers and their special characteristics (ISO 1043-1:2001)

EN ISO 1133, Plastics — Determination of the melt mass-flow rate (MFR) and the melt volume-flow rate (MVR) of thermoplastics (ISO 1133:2005)

EN ISO 1183-1, Plastics — Methods for determining the density of non-cellular plastics — Part 1: Immersion method, liquid pycnometer method and titration method (ISO 1183-1: 2004)

EN ISO 1183-2, Plastics — Methods for determining the density of non-cellular plastics — Part 2: Density gradient column method (ISO 1183-2:2004)

EN ISO 2818, Plastics — Preparation of test specimens by machining (ISO 2818:1994)

EN ISO 10350-1, Plastics — Acquisition and presentation of comparable single-point data — Part 1: Moulding materials (ISO 10350-1:2007)

EN ISO 11357-1, Plastics — Differential scanning calorimetry (DSC) — Part 1: General principles (ISO 11357-1:2009)

ISO 1628-5, Plastics — Determination of the viscosity of polymers in dilute solution using capillary viscometers — Part 5: Thermoplastic polyester (TP) homopolymers and copolymers

ISO 11357-2, Plastics — Differential scanning calorimetry (DSC) — Part 2: Determination of glass transition temperature

ISO 11357-3, Plastics — Differential scanning calorimetry (DSC) — Part 3: Determination of temperature and enthalpy of melting and crystallization

ISO 15527:2007, Plastics — Compression-moulded sheets of polyethylene (PE-UHMW, PE-HD) — Requirements and test methods

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

semi-finished products

rods, hollow bars and panels/plates from which finished parts are manufactured by means of machining

3.2

rods

long, straight and solid products manufactured by means of extrusion, casting or compression moulding and having a uniform circular cross-section over their entire length

3.3

hollow bars

long, straight and hollow products manufactured by means of extrusion, casting or compression moulding and having a uniform circular cross-section, with concentric inside and outside diameter, over their entire length

3.4

panels

plates

flat, rectangular, solid products manufactured by means of extrusion, extrusion, calendaring, casting or compression moulding and having a thickness of at least 0,2 mm which is uniform over their full cross-section

4 Materials

The semi-finished products shall be made of thermoplastic materials (see Table 1). These materials may contain additives such as processing aids, reinforcing agents, fillers, stabilizers or colorants, in which case, they are further referred to in this standard as "modified materials".

The nature and the quantity of these additives can influence the mechanical, thermal and electrical properties of the semi-finished products. The choice and the quantities of additives used are left to the discretion of the manufacturer of the semi-finished products.

Table 1 — List of the thermoplastic materials most commonly used for the manufacture of semi-finished products

Abbreviated terms (according to EN ISO 1043-1:2001)	Materials
ABS	Acrylonitrile-butadiene-styrene
ECTFE	Ethylene-chlorotrifluoroethylene copolymer
PA 6	Polyamide 6
PA 6 C ^a	Polyamide 6, cast
PA 66	Polyamide 66
PA 12	Polyamide 12
PA 12 C ^a	Polyamide 12, cast
PA 46	Polyamide 46
PA 6/12 C ^{ab}	Polyamide 6/12, cast
PBT	Polybutylene terephthalate
PC	Polycarbonate
PEEK	Polyetheretherketone
PE-HD	Polyethylene, high density (Group 2.1 or 3.1 of ISO 15527:2007)
PE-LD	Polyethylene, low density
PE-UHMW	Polyethylene, ultra high molecular weight (Group 1.1 or 1.2 of ISO 15527:2007)
PEI	Polyetherimide
PESU	Polyethersulfone
PET	Polyethylene terephthalate
POM-C	Polyoxymethylene, copolymer
POM-H	Polyoxymethylene, homopolymer
PP-B	Polypropylene, block copolymer
PP-H	Polypropylene, homopolymer
PP-R	Polypropylene, random copolymer
PPE+PS	Polystyrene modified polyphenylene ether
PPS	Polyphenylene sulfide
PPSU	Polyphenylene sulfone
PSU	Polysulfone
PVC-C	Polyvinyl chloride, chlorinated
PVC-HI	Polyvinyl chloride, high-impact modified
PVC-U	Polyvinyl chloride, unplasticized
PVDF	Polyvinylidene fluoride
a	"C" means "cast "
b	PA 6/12 with max. 15 % laurinlactam

5 Requirements

5.1 As-delivered condition

Semi-finished products shall be free of blisters, voids, cracks, foreign matter and other defects which make the product unfit for the intended use. Specific requirements in this respect shall be agreed upon between supplier and customer.

The semi-finished products shall be manufactured in such a way that their internal stress level is minimal (see 5.6.2).

Natural coloured materials: slight variations in hue originating from raw materials and/or manufacturing process are allowed.

Natural colour means that no additives (colorants) are added to the raw materials during their manufacture and processing into semi-finished products for the purpose of obtaining another colour.

Coloration: this shall be uniform and shall be agreed upon between supplier and customer. Slight variations in hue originating from raw materials and/or manufacturing process are allowed.

The testing of the as-delivered condition shall be performed according to 6.4.

NOTE Semi-finished products made from PA are dry after manufacture, but absorb moisture during storage. The moisture content in the as-delivered condition is a function of the type of moulding material, the cross-section (plate thickness, rod diameter or hollow bar wall thickness) of the semi-finished product concerned, as well as the type and period of storage.

Semi-finished products made from POM, PEEK and PP are permitted to have light patches in the centre of the cross-section.

Microporosity in the centre of the cross-section may occur in semi-finished products made from POM-H and PP. The largest diameter or the widest part of the microporosity line(s) shall, however, not exceed 4 %. The procedure for the determination and measurement of microporosity is described in Annex A.

When semi-finished products made from POM and PP are subject to specific requirements, e. g. pressure tightness and/or dielectric strength, they shall be agreed upon between supplier and customer.

5.2 Surface appearance

Semi-finished products shall essentially have smooth surfaces. Shallow marks, grooves and irregularities resulting from the manufacturing process are allowed provided that the product meets the dimensional requirements according to 5.3, 5.4 and 5.5.

Testing of the surface appearance shall be performed according to 6.5.

Specific requirements with respect to the surface appearance are to be agreed upon between supplier and customer.

5.3 Dimensions and tolerances for rods

5.3.1 Diameter

The diameters commonly available are given in the delivery programmes of the suppliers.

The tolerances on the diameters are given in Table 2 for different diameter ranges.

Table 2 — Tolerances on diameters for rods

Diameter ranges	Dimensions in millimetres				
	Column 1 ECTFE PA 6 PA 66 PA 12 PA 46	Column 2 PA 6 C PA 6/12 C PA 12 C	Column 3 ABS PC PEI PESU PPF+PS	Column 4 PE-LD PE-HD PE-UHMW PP-B PP-H	Column 5 PVC-C PVC-HI PVC-U
	PBT		PPSU PSU	PP-R	
up to 4		—		+ 0,3	
over 4 up to 6	+ 0,6 + 0,1	—	+ 0,7 + 0,1	+ 0,1 + 0,4	
over 6 up to 8		—		+ 0,1 + 0,5	
over 8 up to 10	+ 0,7 + 0,1	—	+ 0,8 + 0,1	+ 0,1 + 0,6	
over 10 up to 12		—		+ 0,1 + 0,7	
over 12 up to 16	+ 0,8 + 0,2	—	+ 0,9 + 0,2	+ 0,2 + 0,8	
over 16 up to 18		—		+ 0,2 + 0,9	
over 18 up to 20		—		+ 1,2	
over 20 up to 25	+ 1,0	—	+ 1,2	+ 0,2	
over 25 up to 30	+ 0,2	—	+ 0,2		
over 30 up to 32		—	+ 1,2 + 0,2	+ 1,3	
over 32 up to 36	+ 1,2 + 0,2	+ 1,4 + 0,2	+ 1,6	+ 0,2	
over 36 up to 40			+ 0,2	+ 1,5	
over 40 up to 45	+ 1,3	+ 1,9	+ 2	+ 0,2	+ 2
over 45 up to 56	+ 0,3	+ 0,3	+ 0,3		+ 0,3
over 56 up to 63	+ 1,6 + 0,3	+ 2,5 + 0,3	+ 2,5 + 0,3		+ 2,3 + 0,3
over 63 up to 70				+ 0,3	+ 2,5
over 70 up to 80	+ 2,0 + 0,4	+ 2,8 + 0,4	+ 3,0 + 0,4		+ 0,3 + 3,0
over 80 up to 90	+ 2,2 + 0,5	+ 3,2 + 0,5	+ 3,4 + 0,5	+ 3,4 + 0,5	+ 3,0 + 0,5
over 90 up to 100	+ 2,5 + 0,6	+ 3,5 + 0,6	+ 3,8 + 0,6	+ 3,8 + 0,6	+ 3,5 + 0,6
over 100 up to 110	+ 3,0 + 0,7	+ 3,9 + 0,7	+ 4,2 + 0,7	+ 4,2 + 0,7	+ 4,0 + 0,7
over 110 up to 125	+ 3,5 + 0,8	+ 4,3 + 0,8	+ 4,6 + 0,8	+ 4,6 + 0,8	+ 5,0 + 0,8
over 125 up to 140	+ 3,8 + 0,9	+ 5,0 + 0,8	+ 5,4 + 0,9	+ 5,4 + 0,9	+ 6,0 + 0,9
over 140 up to 150	+ 4,2 + 1,0	+ 5,3 + 0,8	+ 5,8 + 1,0	+ 5,8 + 1,0	+ 7,0 + 1,0
over 150 up to 160	+ 4,5 + 1,1	+ 6,0 + 0,8	+ 6,3 + 1,1	+ 6,3 + 1,1	+ 8,0 + 1,1
over 160 up to 180	+ 5,0 + 1,2	+ 6,5 + 1,0	+ 7,4 + 1,2	+ 7,4 + 1,2	+ 9,0 + 1,2

Table 2 (continued)

Dimensions in millimetres

Diameter ranges	Column 1		Column 2	Column 3	Column 4	Column 5
	ECTFE PA 6 PA 66 PA 12 PA 46 PBT	PEEK PET POM PPS PVDF	PA 6 C PA 6/12 C PA 12 C	ABS PC PEI PESU PPE+PS PPSU PSU	PE-LD PE-HD PE-UHMW PP-B PP-H PP-R	PVC-C PVC-HI PVC-U
over 180 up to 200	+ 5,5 + 1,3	+ 7,5 + 1,0	+ 8,5 + 1,3	+ 8,5 + 1,3	+ 10,0 + 1,3	
over 200 up to 220	+ 5,8 + 1,3	+ 8,5 + 1,0	+ 9,0 + 1,3	+ 9,0 + 1,3	+ 11,0 + 1,3	
over 220 up to 250	+ 6,2 + 1,5	+ 9,5 + 1,0	+ 9,5 + 1,5	+ 9,5 + 1,5	+ 11,0 + 1,5	
over 250 up to 280	+ 6,6 + 1,5	+ 11,0 + 1,0	—	+ 10,0 + 1,5	+ 12,0 + 1,5	
over 280 up to 320	+ 7,5 + 1,5	+ 12,0 + 1,5	—	+ 10,5 + 1,5	—	
over 320 up to 360	+ 8,5 + 1,5	+ 13,5 + 1,5	—	+ 12 + 1,5	—	
over 360 up to 400	+ 9,5 + 1,5	+ 15,0 + 1,5	—	+ 12 + 1,5	—	
over 400 up to 450	+ 10,5 + 1,5	+ 16,5 + 1,5	—	—	—	
over 450 up to 500	+ 11,5 + 1,5	+ 18,0 + 1,5	—	—	—	
over 500 up to 600	—	+ 21 + 3	—	—	—	
over 600 up to 700	—	+ 25 + 3	—	—	—	

Rods made from reinforced materials do not, however, have to meet the tolerances given in their respective column but those in Column 3.

Tolerances on other diameters or deviating tolerances shall be agreed upon between supplier and customer.

NOTE The tolerances in Table 2 apply to rods made from modified and non-modified materials.

5.3.2 Length

The tolerance on length is 0/+ 3 %.

The rods shall have neatly trimmed end faces – perpendicular to their longitudinal axis – so that the nominal length can always be obtained.

Deviating tolerances on the length shall be agreed upon between supplier and customer.

5.3.3 Roundness


The roundness deviation – the difference between the largest and the smallest diameter measured within the same cross-section – shall not be larger than half the tolerance width given in Table 2 for the respective diameter.

5.3.4 Straightness

The deviations of the rods from the straight line extended from edge to edge over the measuring length shall not exceed the values given in Table 3 for different diameter ranges. These limit values refer to a reference length of 1 000 mm (see Figure 1). To allow proper measuring, the rod is laid unconstrained on its side on a flat surface so that the weight of the product does not influence the results. The measured value f is the greatest distance between the straight 1 000 mm measuring ruler and the maximum concave point on the rod.

See Annex B for the conversion of the deflection as a function of the length.

NOTE An example is given in Annex B

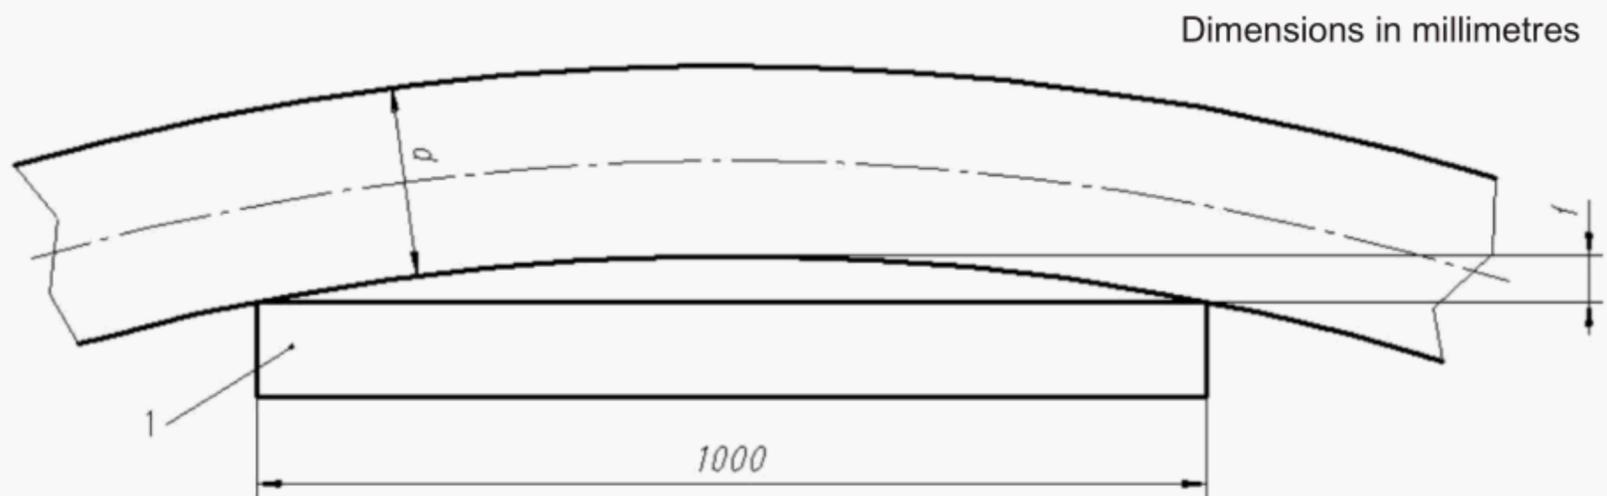

Key

- 1 measuring ruler
- d diameter
- f deviation from straight line

Figure 1 — Principle of the straightness measurement for rods

Table 3 — Straightness requirements for rods

Dimensions in millimetres

Diameter ranges	Max. allowable deviations from straight line ($f_{\max. all.}$)					
	Column 1		Column 2	Column 3	Column 4	Column 5
	non-fibre-reinforced ^a	fibre-reinforced	ECTFE PE-LD PE-HD PVDF	PE-UHMW	PP-H PP-B PP-R	PVC-C PVC-HI PVC-U
up to 20	8,0	10,0	15,0	20,0	10,0	10,0
over 20 up to 32	5,0	6,5	12,0	17,5	8,0	8,0
over 32 up to 50	4,0	5,0	10,0	17,5	8,0	8,0
over 50 up to 100	4,0	5,0	8,0	15,0	6,5	6,5
over 100 up to 150	3,5	4,0	6,0	10,0	5,0	5,0
over 150	3,5	4,0	6,0	10,0	5,0	5,0

Special straightness requirements shall be agreed upon between supplier and customer.

NOTE The limit values given in Columns 2 to 5 apply to rods made from modified and non-modified materials.

a Additives other than fibres can be included in the materials.

5.4 Dimensions and tolerances for hollow bars

5.4.1 Diameters

The diameters commonly available are given in the delivery programmes of the suppliers.

The tolerances on the outside and inside diameters are given in Table 4 for different diameter ranges.

Table 4 — Tolerances on diameters for hollow bars

Outside diameter ranges	Dimensions in millimetres			
	Tolerances on outside diameter	Tolerances on outside diameter	Tolerances on inside diameter	Tolerances on inside diameter
	ABS, ECTFE, PA 6, PA 66, PA 12, PA 46, PBT, PC, PEEK, PET, PEI, PESU, POM, PPE+PS, PPS, PPSU, PSU, PVDF	PA6 C, PA12 C, PA 6/12 C	ABS, ECTFE, PA 6, PA 66, PA 12, PA 46, PBT, PC, PEEK, PET, PEI, PESU, POM, PPE+PS, PPS, PPSU, PSU, PVDF	PA6 C, PA12 C, PA 6/12 C
from 20 up to 30	+ 1,1	+ 3,0	- 0,4	- 0,8
over 30 up to 50	+ 0,4		- 1,1	
over 50 up to 60	+ 2,0	+ 0,8	- 0,6	- 4,0
over 60 up to 80	+ 0,6	- 0,8		
over 80 up to 110	+ 2,5	+ 4,0	- 2,5	- 0,8
over 110 up to 150	+ 0,8	+ 0,8	- 0,8	
over 150 up to 180	+ 3,0	+ 5,0	- 3,0	- 4,0
over 180 up to 220	+ 0,8	+ 1,0	- 1,6	
over 220 up to 250	+ 3,6	+ 7,5	- 5,0	- 6,0
over 250 up to 300	+ 1,2	+ 1,5	- 2,0	
over 300 up to 400	+ 4,5	+ 9,0	- 6,5	- 1,5
over 400 up to 500	+ 1,5	+ 11,0	- 2,2	
over 500 up to 600	+ 5,4	+ 1,8	- 7,5	- 1,8
	+ 1,8	+ 2,0	- 2,5	
	+ 6,0	+ 12,5	- 8,5	- 9,0
	+ 2,0	+ 2,5	- 2,5	
	+ 9,0	+ 15,0	- 3,0	- 11,0
	+ 3,0	+ 3,0	- 3,5	
	+ 10,0	+ 17,5	- 12,0	- 12,5
	+ 3,0	+ 20,0	- 3,5	
	+ 11,0	+ 3,0	- 13,0	- 3,0
	+ 3,0	+ 3,0	- 3,5	
	+ 13,0	+ 3,0	- 14,0	- 3,0
	+ 3,0	+ 3,0	- 16,0	
	+ 15,0	+ 25,0	- 3,5	- 20,0
	+ 3,0	+ 3,0	- 18,0	- 3,0
	+ 3,0	+ 3,0	- 18,0	- 25,0

Tolerances for other diameters or deviating tolerances shall be agreed upon between supplier and customer.

NOTE 1 The tolerances in Table 4 apply to hollow bars made from modified and non-modified materials.

NOTE 2 The tolerances in Table 4 can also be used for hollow bars made from PE and PP provided that there are no other specific standards for these materials.

5.4.2 Length

The tolerance on length is 0/+ 3 %.

The hollow bars shall have neatly trimmed end-faces – perpendicular to their longitudinal axis – so that the nominal length can always be obtained.

Deviating tolerances on the length shall be agreed upon between supplier and customer.

5.4.3 Roundness


The roundness deviation on the inside and outside diameter – the difference between the largest and the smallest diameter measured within the same cross-section – shall not be larger than half the tolerance range given in Table 4 for the respective diameters.

5.4.4 Straightness

The deviations of the hollow bars from the straight line extended from edge to edge over the measuring length shall not exceed the values given in Table 5 for different outside diameter ranges. These limit values refer to a reference length of 1 000 mm (see Figure 2). To allow proper measuring, the hollow bar is laid unconstrained on its side on a flat surface so that the weight of the product does not influence the results. The measured value f is the greatest distance between the straight, 1 000 mm long, measuring ruler and the concave point of the hollow bar.

See Annex B for the conversion of the deflection as a function of the length.

Dimensions in millimetres

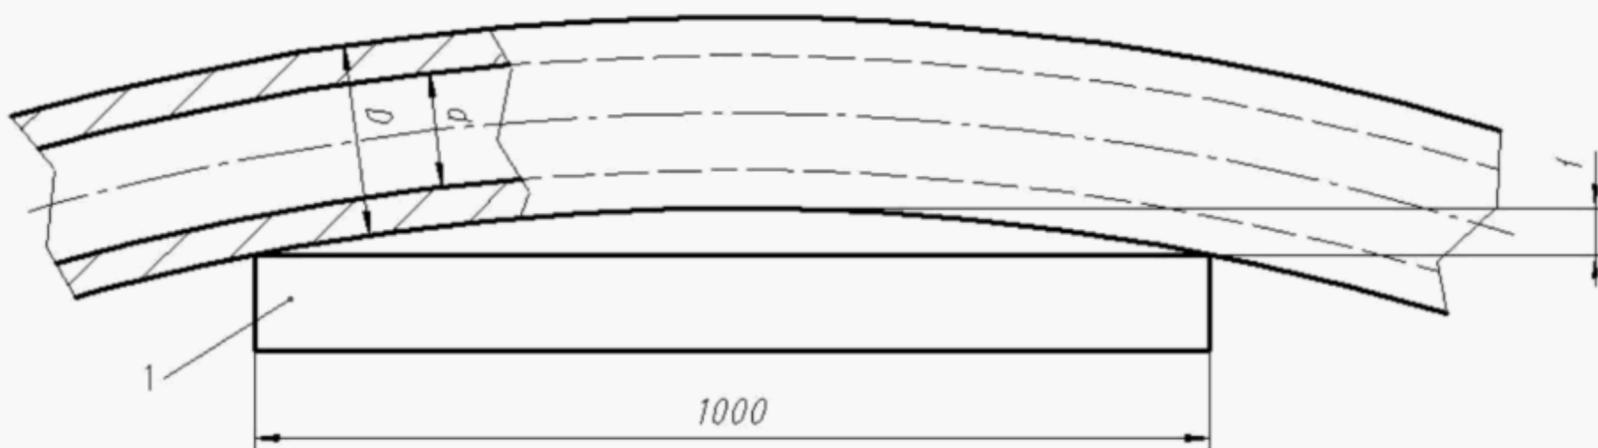

Key

- 1 measuring ruler
- d inside diameter
- D outside diameter
- f deviation from straight line

Figure 2 — Principle of the straightness measurement for hollow bars

Table 5 — Straightness requirements for hollow bars

Outside diameter ranges	Dimensions in millimetres
	Maximal allowable deviations from the straight line
	(f _{max. all.})
up to 20	10
from 20 up to 45	6
over 45 up to 100	5
over 100	4

Special straightness requirements shall be agreed upon between supplier and customer.

NOTE The limit values given in Table 5 apply to hollow bars made from modified and non-modified materials.

5.4.5 Concentricity

In order to allow machining of the nominal outside and nominal inside diameter from the hollow bar when clamping both on the outside or the inside diameter, the eccentricity – the deviation between the centres of inside and outside diameter ($\Delta E/2$) – shall be such that the difference in wall thickness ΔE is less than or equal to $0,8 \cdot (d_{\text{nom}} - d_{\text{max}})$ and less than or equal to $0,8 \cdot (D_{\text{min}} - D_{\text{nom}})$.


$$\Delta E = E_{\text{max}} - E_{\text{min}} \leq 0,8 \cdot (d_{\text{nom}} - d_{\text{max}})$$

and

$$\Delta E = E_{\text{max}} - E_{\text{min}} \leq 0,8 \cdot (D_{\text{min}} - D_{\text{nom}})$$

where

- E_{max} is the maximum wall thickness in cross-section;
- E_{min} is the minimum wall thickness in cross-section;
- d_{nom} is the nominal inside diameter;
- d_{max} is the measured maximum inside diameter;
- D_{nom} is the nominal outside diameter;
- D_{min} is the measured minimum outside diameter.

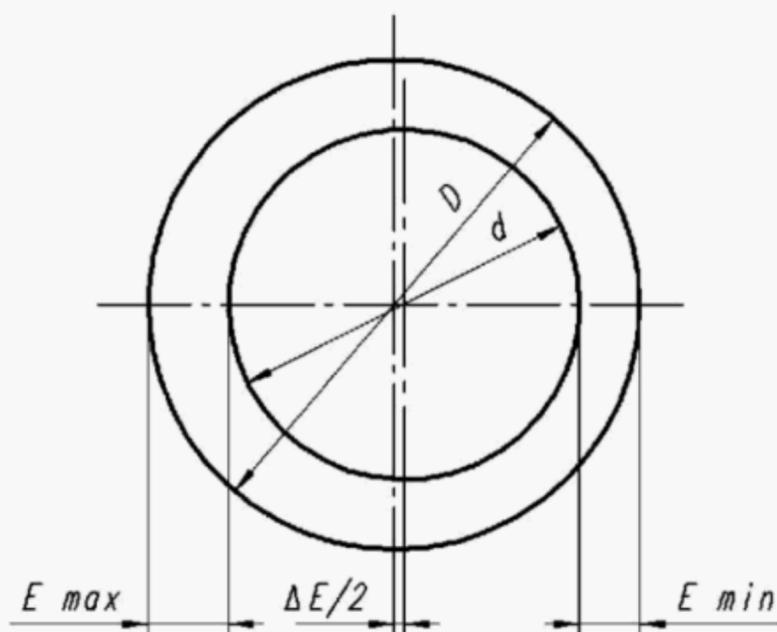

Key
D outside diameter
d inside diameter
 E_{max} maximum wall thickness in cross-section
 E_{min} minimum wall thickness in cross-section
 $\Delta E/2$ concentricity deviation

Figure 3 — Principle of the concentricity measurement

5.5 Dimensions and tolerances for panels/plates

5.5.1 Thickness

The thicknesses generally available are given in the delivery programmes of the suppliers.

The tolerances on thicknesses are given in Tables 6 and 7 for different thickness ranges.

Table 6 — Tolerances on the thicknesses for calendered panels/plates

Dimensions in millimetres

Thickness	Tolerances ABS, ECTFE, PA 6, PA 66, PA 12, PA 46, PBT, PEEK, PEI, PESU, PET, POM, PPE+PS, PPS, PPSU, PSU
0,2 to 0,5	± 0,05
over 0,5 to 1,2	± 0,10
over 1,2 to 2,5	± 0,15
over 2,5 to 4	± 0,20
over 4 to 6	± 0,25
NOTE	ISO 15014 and EN ISO 11963 are applicable for tolerances on PVDF and PC respectively.

Table 7 — Tolerances on thicknesses for extruded, cast and compression-moulded panels/plates

Thickness	Dimensions in millimetres	
	Tolerances ABS, ECTFE, PA 6, PA 66, PA 12, PA 46, PBT, PC, PEEK, PEI, PESU, PET, POM, PPE+PS, PPS, PPSU, PSU, PVDF	Tolerances PA 6 C, PA 12 C, PA 6/12 C
from 5 to 6	+ 0,7	+ 1,5
over 6 to 10	+ 0,2 + 1,1	+ 0,2
over 10 to 25	+ 0,2 + 1,5	+ 2,5
over 25 to 50	+ 0,3 + 2,5	+ 0,3 + 3,5
over 50 to 70	+ 0,5 + 3,5	+ 0,5 + 5,0
over 70 to 100	+ 0,5 + 5,0	+ 0,5 + 7,0
over 100 to 130	+ 0,5 + 6,0	+ 0,5 + 9,0
over 130 to 160	+ 0,5 + 7,0	+ 0,5 + 10,0
<p>Tolerances for other thicknesses or deviating tolerances shall be agreed upon between supplier and customer.</p> <p>NOTE 1 The tolerances in Table 7 apply to panels/plates made from modified and non-modified materials.</p> <p>NOTE 2 The tolerances in Table 7 can also be used for panels/plates made from PE and PP provided that there are no other specific standards for these materials.</p> <p>NOTE 3 Tolerances for PVDF and PC apply only to the thickness ranges not given in ISO 15014 or EN ISO 11953 respectively.</p>		

5.5.2 Length and width

- Tolerance on width: + 0,5 %/+ 4 %
- Tolerance on length: + 0 %/+ 3 %

Deviating tolerances on width and/or length shall be agreed upon between supplier and customer.

The plates shall have neatly trimmed end faces perpendicular to the axes of symmetry so that the nominal length and/or nominal width can always be obtained.

5.5.3 Straightness


The deviations of the panels/plates from the straight line extended from edge to edge over the measuring length shall not exceed the values given in Table 8 for different thickness ranges. These limit values refer to a reference length of 1 000 mm (see Figures 4a), 4b) and 4c)). To allow proper measuring, the panel/plate is laid unconstrained on a flat surface so that the concave side is uppermost.

The measured value f is the maximum distance between the straight, 1 000 mm long, measuring ruler and the concave side of the panel/plate l , measured over the longest length or width.

See Annex B for the conversion of the deflection as a function of the length.

NOTE An example is given in Annex B.

Dimensions in millimetres

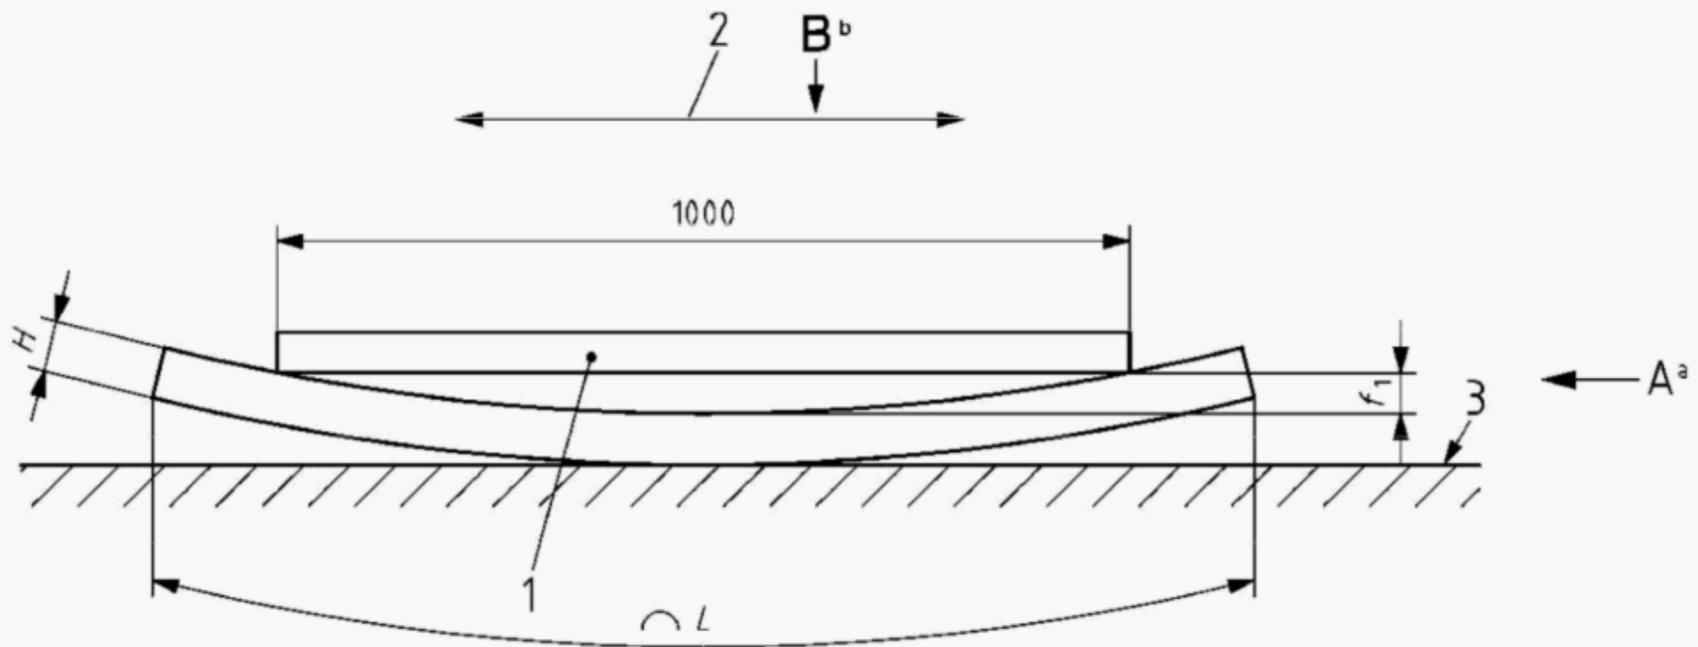


Key

- 1 measuring ruler
- 2 direction of extrusion (if applicable)
- 3 flat surface H thickness
- L length
- f_1 deviation from straight line
- A^a side view
- B^b top view

a) Principle of straightness measurement on panels/plates over the length (L)

Dimensions in millimetres

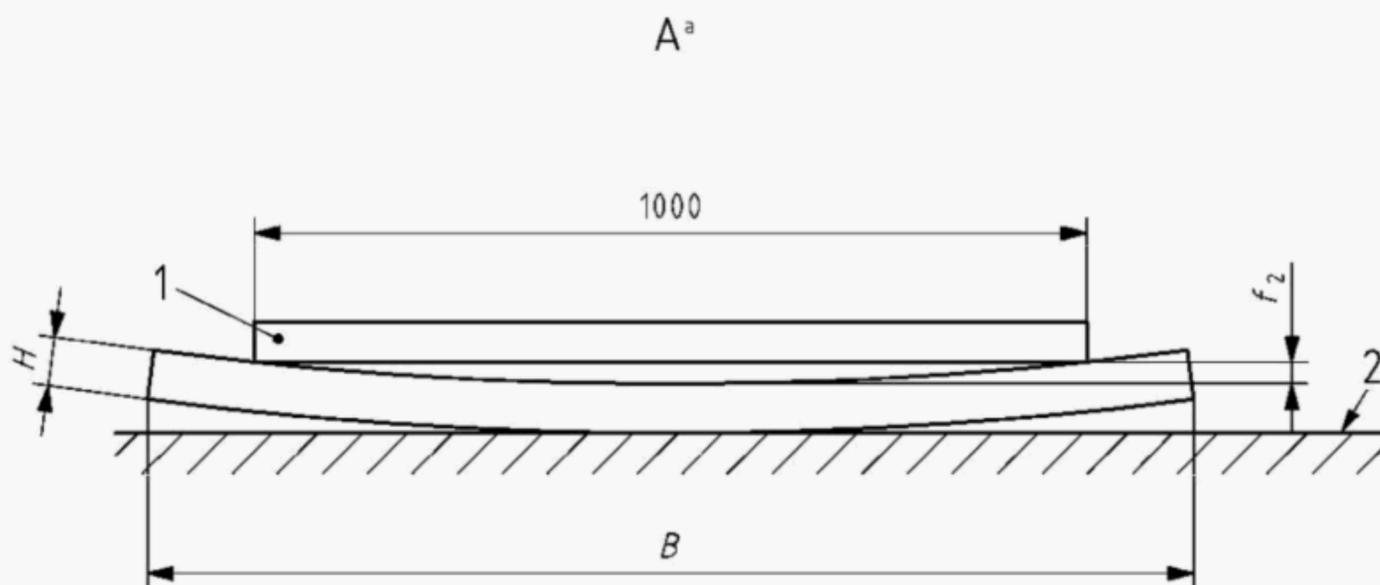


Key

- 1 measuring ruler
- 2 flat surface
- H thickness
- B width
- f_2 deviation from straight line

b) Principle of the straightness measurement on panels/plates over the width (B)

Dimensions in millimetres

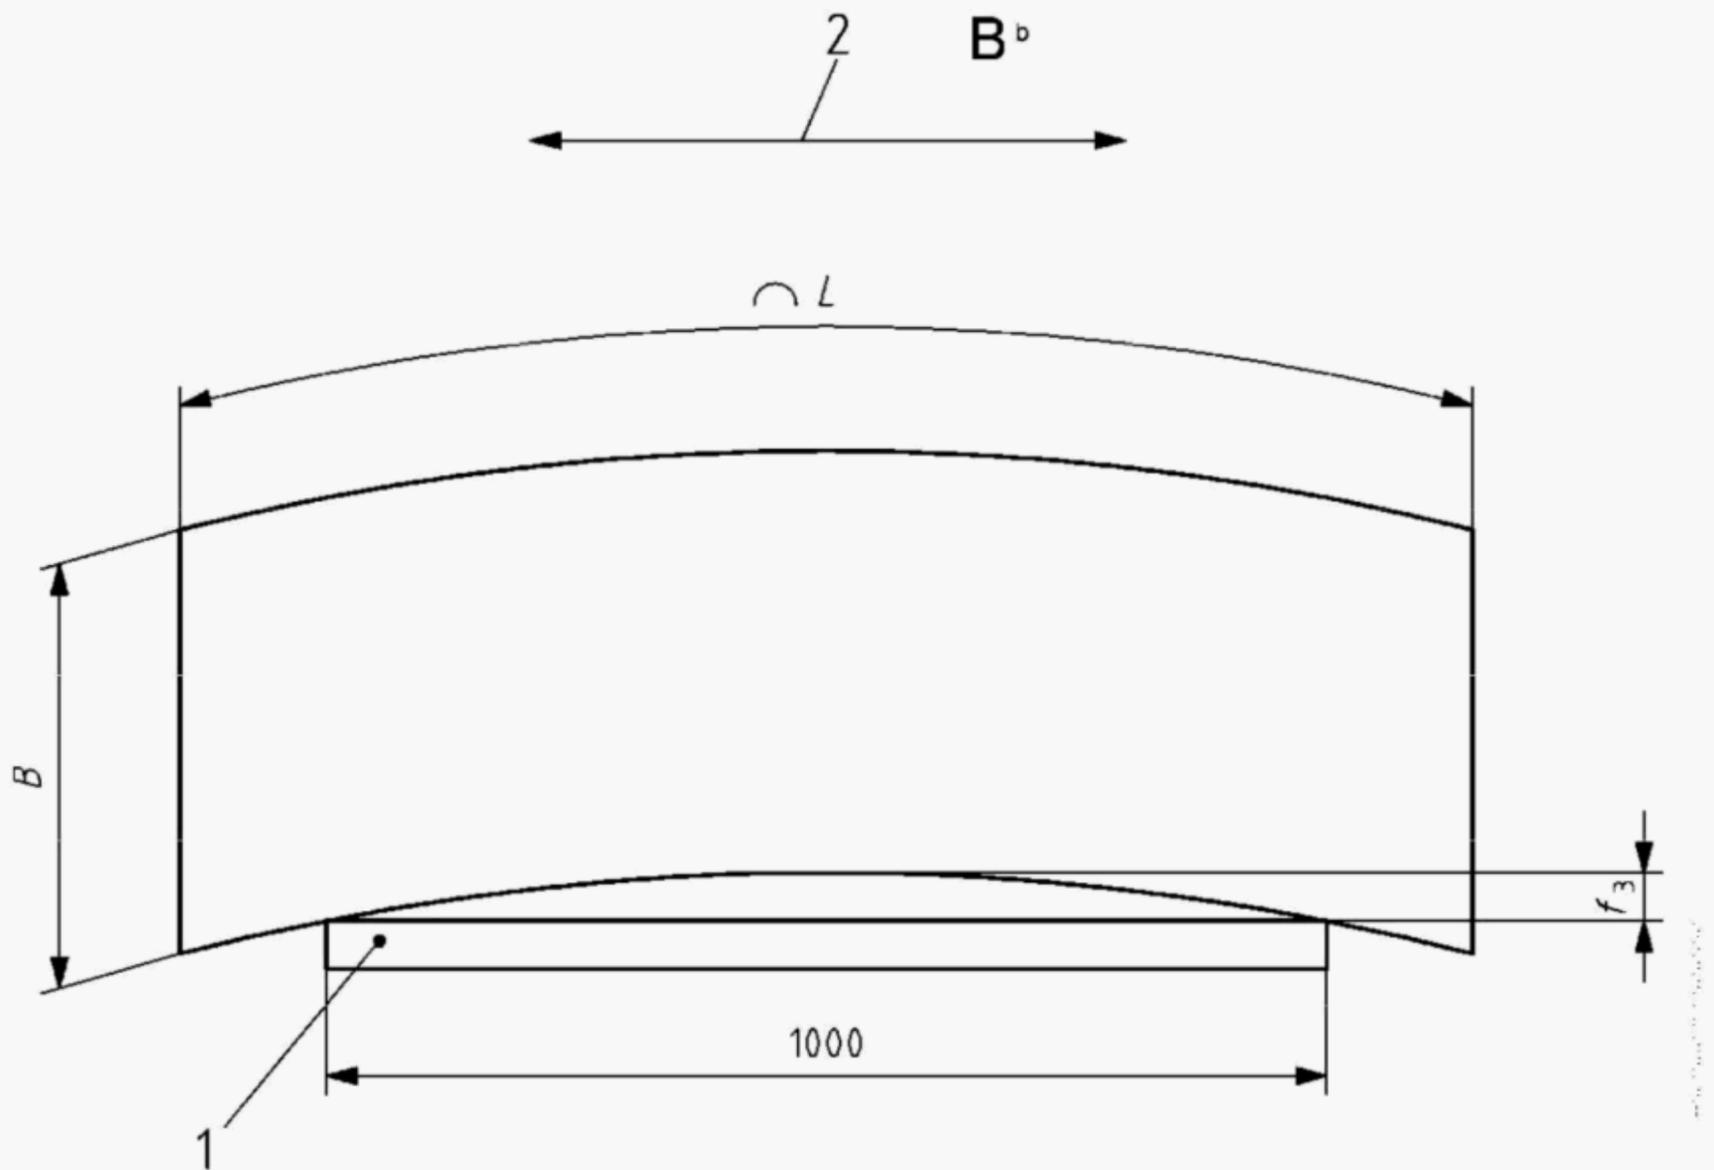

Key

- 1 measuring ruler
- 2 direction of extrusion (if applicable)
- 3 flat surface
- L length
- B width
- f_3 deviation from straight line

c) Principle of the straightness measurement on panels/plates along the edges

Figure 4 — Principle of the straightness measurement on panels/plates

Table 8 — Straightness requirements for panels/plates

Dimensions in millimetres

Thickness ranges	Maximal allowable deviations from the straight line ($f_{\max. \text{ all.}}$)					
	ABS	ECTFE	PA 6	PA 6 C	PA 66	PA 12
	PA 12 C	PA 6/12 C	PA 46	PBT	PC	PEEK
	PEI	PESU	PET	POM	PPE+PS	PPS
	PPSU	PSU	PVDF			
	f ₁ (see Figure 4a))		f ₂ (see Figure 4b))		f ₃ (see Figure 4c))	
up to 6	6,0		7,0		4,0	
over 6 up to 16	4,0		5,0			
over 16 up to 25	2,5		3,5			
over 25 up to 50	2,0					
over 50	1,5					
Deviating straightness requirements shall be agreed upon between supplier and customer.						
NOTE The limit values in Table 8 apply to unmachined panels/plates made from modified and non-modified materials.						

5.6 Properties

5.6.1 Physical properties

The property values below apply only to semi-finished products made from non-modified materials in natural colour (measured on test specimens machined from the semi-finished products). The property values or special requirements for modified materials are to be agreed upon between supplier and customer.

The property values of semi-finished products made from thermoplastic materials depend mainly on their thermal history and morphology, and, therefore, on the respective shape (rod, hollow bar, panel/plate) and dimension (diameter or thickness). This makes it very difficult to give limit values that apply to all shapes and dimensions. As a consequence, the values given in the Tables 9 and 10 for density, tensile stress at yield, elongation at break, tensile modulus of elasticity, melting temperature/glass transition temperature and Vicat softening temperature VST/B/50 are not minimum values but guideline values (in italics). They are typical average values from tests on rods of diameter 40 mm to 60 mm, mainly to be used for comparative purposes when selecting a material for a given application. Although these values fall within the normal range of product properties, they are, however, not assured and should not be used to establish material specification limits.

Property values to be used for establishing material specification limits shall be agreed upon between supplier and customer as a function of the shape and dimension(s) concerned.

In the case of melt volume flow rate and viscosity number, these are minimum values.

Table 9 — Property values for semi-finished products made from ABS, ECTFE, PA, PBT, PC, PEEK, PEI, PESU, PET, POM, PPE+PS, PPS, PPSU, PSU and PVDF

Properties	Unit	Materials											Testing according to subclause
		ABS	ECTFE	PA 6	PA 6 C	PA 66 ^a	PA 12	PA 12 C	PA 46	PA 6/12 C	PBT	PC	
Density	g/cm ³	1,04	1,70	1,14	1,15	1,14	1,01	1,02	1,19	1,13	1,32	1,20	6.7
Tensile stress at yield	MPa	40	30	80	80	90	50	60	100	75	65	70	6.8
Elongation at break	%	50	> 50	> 50	40	40	> 50	> 50	30	> 50	15	> 50	6.8
Tensile modulus of elasticity	MPa	2 000	1 600	3 200	3 300	3 400	1 800	1 900	3 250	2 800	2 800	2 300	6.9
Melt volume-flow rate MVR	cm ³ /10 min	≤ 6	≤ 5	NA ^c	NA ^c	NA ^c	NA ^c	NA ^c	NA ^c	NA ^c	NA ^c	≤ 8	6.11
Melting temperature (*) or glass transition temperature (**)	°C	109 (**)	225 (*)	220 (*)	217 (*)	260 (*)	180 (*)	175 (*)	290 (*)	212 (*)	225 (*)	150 (**)	6.12
Viscosity number	ml/g	NA ^c	NA ^c	≥ 220 ^b	NM ^d	≥ 220	≥ 190	NM ^d	≥ 120 ^b	NM ^d	≥ 130	NA ^c	6.13

a For processing reasons, PA 6 can be added for semi-finished products made from PA 66.

b Based on the use of sulfuric acid as solvent.

c "NA" means "not applicable".

d "NM" means "not measurable".

Table 9 (continued)

Properties	Unit	Materials											Testing according to subclause
		PEEK	PEI	PESU	PET	POM-C	POM-H	PPE + PS	PPS	PPSU	PSU	PVDF	
Density	g/cm ³	1,31	1,28	1,37	1,38	1,41	1,42	1,06	1,35	1,29	1,24	1,78	6.7
Tensile stress at yield	MPa	110	120	90	90	65	75	50	95	80	85	58	6.8
Elongation at break	%	15	10	20	15	40	50	25	5	> 50	10	25	6.8
Tensile modulus of elasticity	MPa	4 100	3 300	2 600	3 350	2 800	3 300	2 100	3 400	2 400	2 700	2 000	6.9
Melt volume-flow rate MVR	cm ³ /10 min	≤ 12	≤ 16	NV ^e	NA ^c	≤ 3,5	≤ 3,5	≤ 12	NV ^e	≤ 18	≤ 8	≤ 6	6.11
Melting temperature (*) or glass transition temperature (**)	°C	343 (*)	218 (**)	230 (**)	250 (*)	165 (*)	175 (*)	140 (**)	280 (*)	225 (**)	190 (**)	176 (*)	6.12
Viscosity number	ml/g	NA ^c	NA ^c	NA ^c	≥ 100	NA ^c	6.13						
<p>c "NA" means "not applicable".</p> <p>e "NV" means "no values available".</p>													

Table 10 — Property values for semi-finished products made from PE, PP und PVC

Properties	Unit	Materials										Testing according to subclause
		PE-LD	PE-HD Group 3.1	PE-HD Group 2.1	PE-UHMW	PP-H	PP-B	PP-R	PVC-C	PVC-HI	PVC-U	
Density	g/cm ³	0,92	0,95	0,96	0,93	0,90	0,90	0,90	1,60	1,40	1,44	6.7
Tensile stress at yield	MPa	10	23	29	19	32	26	25	60	52	54	6.8
Elongation at break	%	> 50	> 50	> 50	> 50	> 50	> 50	> 50	15	22	15	6.8
Tensile modulus of elasticity	MPa	250	900	1 200	600	1 400	1 200	1 000	2 900	2 700	3 100	6.9
Vicat softening temperature VST/B/50	°C	50	70	80	80	90	60	60	103	74	78	6.10
Melt volume-flow rate MVR	cm ³ /10 min	≤ 0,5	≤ 2,0 ^f ≤ 30,0 ^g	≤ 0,15 ^f ≤ 5,0 ^g	NM ^d	≤ 0,6	≤ 0,6	≤ 0,4	≤ 121	NV ^e	≤ 83	6.11
Melting temperature (*) or glass transition temperature (**)	°C	115 (*)	136 (*)	138 (*)	135 (*)	167 (*)	167 (*)	150 (*)	121 (**)	NV ^e	NV ^e	6.12
<p>d "NM" means "not measurable".</p> <p>e "NV" means "no values available".</p> <p>f "Values for 190°C/5kg".</p> <p>g "Values for 190°C/21,6kg".</p>												

5.6.2 Dimensional stability after heat treatment

The dimensional stability after heat treatment is determined by means of the test described in 6.14.

The relative changes in length, thickness and diameter of semi-finished products made from non-modified materials such as polyamide (PA), polybutylene terephthalate (PBT), polycarbonate (PC), polyetheretherketone (PEEK), polyethylene terephthalate (PET), polyoxymethylene (POM), polystyrene modified polyphenylene ether (PPE+PS) and polyvinylidenefluoride (PVDF) shall not exceed the guideline values given in Table 11 derived from measurements from panels 20 mm high and rods with a diameter of 50 mm to 60 mm..

NOTE There are no values available yet for the other materials listed in Table 1.

Table 11 — Guideline values for the relative dimensional changes

Type of semi-finished product	Dimensions mm	Guideline values for the relative dimensional changes													
		PA 6	PA 6,C	PA 66	PA 12	PA 12,C	PA 46	PA 6/12 C	PBT	PC	PEEK	PET	PPE+ PS	POM	PVDF
Rods	$d \geq 12$ to ≤ 200	1,75%	1,5%	1,5%	1,5%	1,0%	1,5%	1,5%	1,25%	0,25%	1,0%	1,0%	0,25%	0,75%	1,0%
Hollow bars	$D \leq 300$ and $E \leq 40$														
Panels/plates	$H \geq 5$ to ≤ 100	0,75%	0,5%	0,75%	1,0%	0,5%	1,0%	0,5%	0,75%	0,25%	1,0%	0,75%	0,25%	0,5%	0,75%
NOTE		These figures apply to semi-finished products with a moisture content of $\leq 0,2\%$													

5.6.3 Physiological behaviour

The requirements specified by the different applicable regulations shall be met when the semi-finished products are further used for the manufacture of articles intended to come into contact with foodstuffs and confectionery.

Specific requirements with respect to their suitability for contact with foodstuffs and/or drinking water or for use in medical devices shall be agreed upon between supplier and customer.

6 Test methods

6.1 Test conditions

Unless otherwise stated in 6.7 to 6.15 or otherwise agreed between supplier and customer, the tests are carried out in a standard atmosphere at (23 ± 2) °C according to EN ISO 291:2008 on dry test specimens.

In the case of polyamides, the test specimens shall be dried prior to testing in a vacuum oven at 80 °C until constant weight is achieved followed by storage of at least 16 hours in a desiccator at (23 ± 2) °C. After removal from the desiccator, the tests shall be carried out immediately.

6.2 Sampling size


The type and number of semi-finished products belonging to a delivery that have to be tested shall be derived from the respective standards or be agreed between supplier and customer.

6.3 Test specimen preparation

6.3.1 Mechanical properties


The test specimens shall be taken as shown in Figures 5, 6 and 7 by means of machining from the semi-finished product in the extrusion direction/longitudinal direction according to the requirements of EN ISO 2818.

Deviating procedures, e. g. taking the test specimens perpendicular to instead of parallel with the extrusion direction, shall be agreed between supplier and customer.

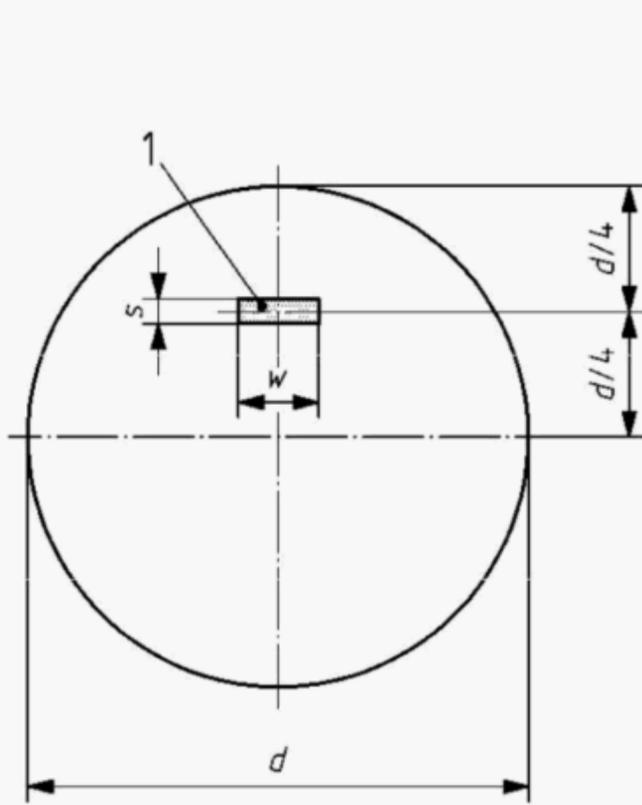


Key
1 test specimen
s thickness
w width
d diameter

Figure 5 — Taking test specimens from rods

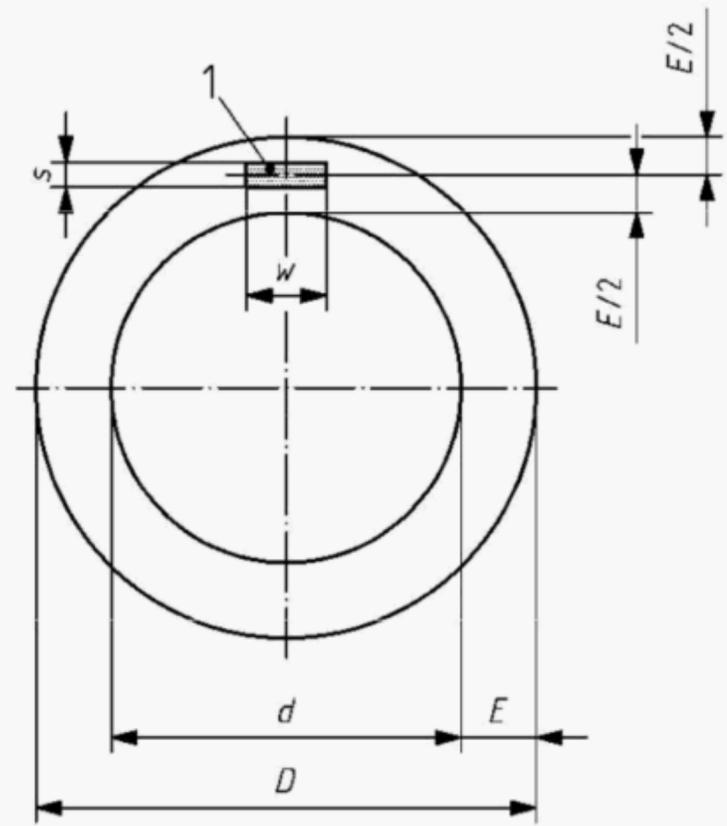

Key
1 test specimen
s thickness
w width
d inside diameter
D outside diameter
E wall thickness

Figure 6 — Taking test specimens from hollow bars

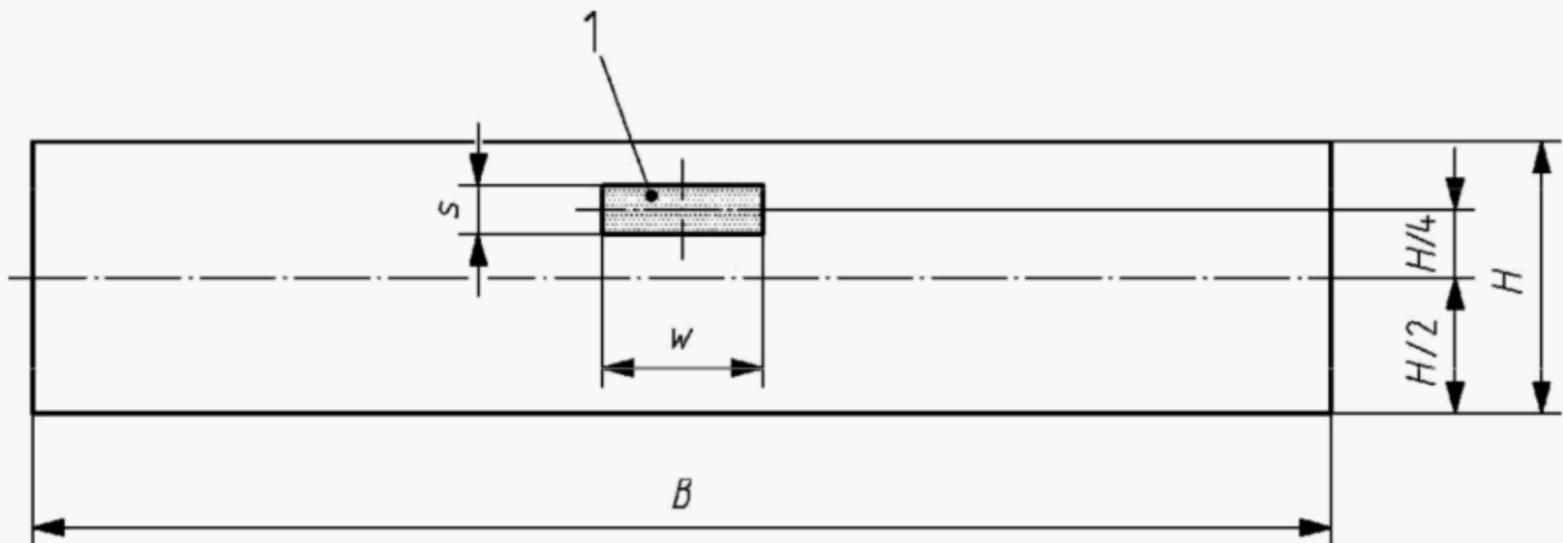

Key
1 test specimen
s thickness
w width
H panel thickness
B panel width

Figure 7 — Taking test specimens from panels/plates

The test specimen shall be free from surface defects which may give rise to notch effects. Burrs created during machining shall be removed without, however, damaging the surfaces, e.g. creating notches. If

necessary, the test specimen surfaces shall be finished with abrasive paper – grain size 240 or finer – or other suitable means. This finishing operation shall be carried out parallel to the long side of the test specimens.

6.3.2 Density

The test specimens shall be taken from the semi-finished products at the positions shown in Figures 5, 6 and 7. During this operation, the material shall not be deformed, overheated or melted.

6.3.3 Melt volume-flow rate, viscosity number, melting temperature/glass transition temperature

The test specimens, in the form of granules or chips, shall be taken from the semi-finished products at the positions shown in Figures 5, 6 and 7. Care shall be taken that the material is not overheated or melted during this operation. If moisture-sensitive materials are not tested directly after sampling, the test specimens shall be stored in a desiccator with a drying agent. The testing itself shall be carried out on dry test specimens.

6.3.4 Dimensional stability after heat treatment


6.3.4.1 Rods/hollow bars

Three test specimens having a length (l) of $(25 \pm 0,1)$ mm shall be taken at least 30 mm from the end faces of the rod or hollow bar. The test specimen diameter shall be the same as in the “as-delivered” condition so that the diameter of the test specimen is equal to the diameter of the rod or hollow bar. The end faces of the test specimens shall be machined (turned/milled) to be plane-parallel and smooth; see Figures 9 and 10.

6.3.4.2 Panels/plates

Three test specimens of rectangular shape $(50 \pm 0,2)$ mm (milled/planed) x (60 ± 1) mm (saw-cut) (rectangular blocks) shall be machined from the panels/plates. The test specimens are taken uniformly over the width of the plate as shown in Figure 8. The thickness shall be the same as in the “as-delivered” condition so that the test specimen thickness is equal to the plate thickness.

Dimensions in millimetres

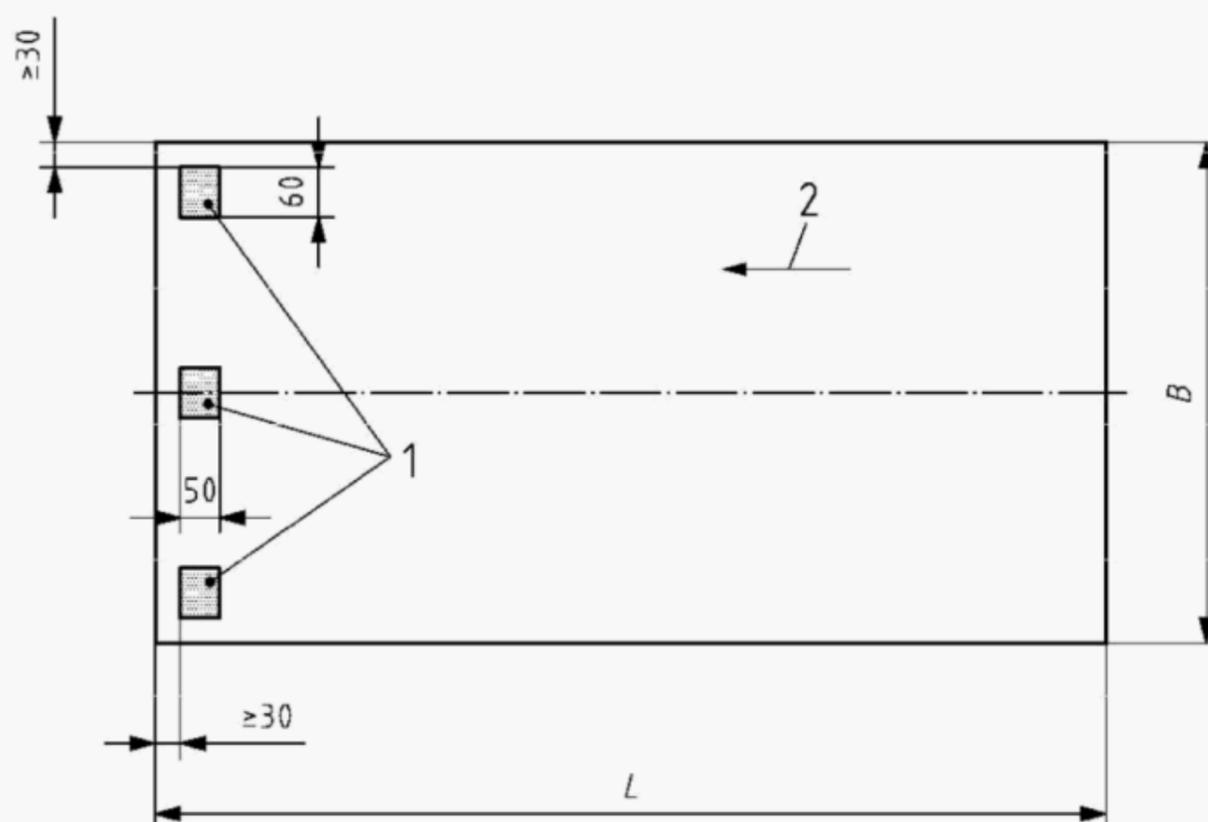

Key

- 1 test specimens
- 2 direction of extrusion (if applicable)
- L length of panel B width of panel

Figure 8 — Taking test specimens from panels/plates

6.4 As-delivered condition

The surfaces shall be assessed visually and without the use of optical instruments for blisters, gouges, voids, cracks or other defects. Testing for internal defects may be carried out by means of ultrasound or alternatively by means of optical checking of the trimmed edges.

6.5 Surface appearance

The surface appearance shall be assessed visually and without the use of optical instruments. Possible marks and irregularities shall be evaluated by machining to nominal size.

6.6 Accuracy of the dimension measuring instruments

The accuracy of measurement of the instruments used for the determination of the diameter, thickness and straightness of the semi-finished products should be 0,1 mm. The accuracy of measurement for the determination of width and length of the semi-finished products should be 1 mm.

6.7 Density

The density shall be determined according to EN ISO 1183-1 or EN ISO 1183-2 on at least 3 test specimens each having a minimum mass of 1 g.

6.8 Tensile stress at yield and elongation at break

The tensile stress at yield and the elongation at break shall be determined according to EN ISO 527-1 and EN ISO 527-2:1996 on at least 5 test specimens of type 1B.

The testing speed shall be 5 mm/min or 50 mm/min, to be chosen as a function of the ductile behaviour of the material (tough or brittle) according to EN ISO 10350-1.

6.9 Tensile modulus of elasticity

The tensile modulus of elasticity shall be determined according to EN ISO 527-1 and EN ISO 527-2:1996 on at least 5 test specimens of type 1B. The testing speed shall be 1 mm/min with a permissible deviation of $\pm 20\%$.

6.10 Vicat softening temperature

The Vicat softening temperature VST/B/50 shall be determined according to EN ISO 306 on at least 2 test specimens.

6.11 Melt volume-flow rate (MVR)

The melt volume-flow rate MVR shall be determined according to EN ISO 1133 on at least 1 test specimen, using the temperature/load-combination given in Table 12 for the respective material.

Table 12 — Test conditions for determination of the melt volume-flow rate (MVR)

Material	Temperature °C	Load kg
ECTFE	275	5
ABS	220	10
PC	300	1,2
PEEK	380	5
PE-HD ^b	190	5
PE-HD ^b	190	21,6
PE-LD	190	2,16
PE-UHMW ^a	190	21,6
PEI	360	5
PESU	380	2,16
POM	190	2,16
PP	230	2,16
PPE+PS	280	5
PPS	315	5
PPSU	365	5
PSU	343	2,16
PVDF	230	5
a Not measurable		
b Both methods applicable		

6.12 Melting temperature/glass transition temperature

The melting temperature (peak melting temperature T_{pm}) shall be determined according to EN ISO 11357-1 and ISO 11357-3 from the second heat scan, using a heating rate of 10 °C/min.

The glass transition temperature shall be determined according to EN ISO 11357-1 and ISO 11357-2 from the second heat scan, using a heating rate of 20 °C/min.

6.13 Viscosity number

The viscosity number shall be determined for the materials listed in Table 13 on at least 2 test specimens. The solvent and the test method shall also be selected from Table 13.

Table 13 — Test methods and solvents to be used for determination of the viscosity number

Material	Solvents	Test methods
PA 6 PA 6 C PA 66 PA 46 PA 6/12 C	Sulfuric acid (96 ± 0,15) % m/m Formic acid (90 ± 0,15) % m/m	EN ISO 307
PA 12 PA 12 C	m-cresol 99 % m/m minimum	EN ISO 307
PBT PET	Solution of 50 parts by mass of phenol and 50 parts by mass of 1,2-dichlorobenzene	ISO 1628-5

6.14 Dimensional stability after heat treatment

The dimensional stability after heat treatment shall be determined on dry test specimens and after adequate temperature equilibrium has been reached:

The test specimen length (l) of rods and hollow bars or thickness (h) of panels/plates is measured to the nearest of 0,01 mm in the standard atmosphere at (23 ± 2) °C. This is done in the centre of the cylindrical test specimen (in the case of rods) and in the centre of the rectangular test specimen (in the case of panels/plates) or at two marked positions offset by 180° in the middle of the wall thickness (in the case of hollow bars); see Figures 9, 10 and 11.

The diameter of each test specimen (d in the case of rods and D in the case of hollow bars) is measured to the nearest 0,01 mm in the standard atmosphere at (23 ± 2) °C. This is done at two marked positions offset by 90° and at mid-length (see Figures 9 and 10).

For panels/plates, the width (nominal size 50 mm) of each rectangular test specimen is measured to the nearest 0,01 mm in the standard atmosphere at (23 ± 2) °C. This is done in the middle of the test specimen thickness and length (see Figure 11).

The test specimens are put in an air oven with forced air circulation which is then to be heated to the temperature indicated in Table 14 for the material concerned, using a heating rate of 10 °C/h to 20 °C/h. Once the test temperature is reached, it is maintained for 6 h. In the next step, the test specimens are cooled down in the oven to room temperature at a cooling rate of 10 °C/h to 20 °C/h. They are then left in standard air atmosphere at (23 ± 2) °C for at least 12 h (temperature equilibrium) before they are measured again as described above to the nearest 0,01 mm, at the same positions as during the first measurements.

The relative dimensional changes in length, thickness, width, thickness or diameter are determined as average values and calculated as follows:

$$\Delta_l = \frac{l_s - l_E}{l_s} \times 100$$

and/or

$$\Delta_h = \frac{h_s - h_E}{h_s} \times 100$$

and/or

$$\Delta_b = \frac{b_s - b_E}{b_s} \times 100$$

and/or

$$\Delta_d = \frac{d_s - d_E}{d_s} \times 100$$

and/or

$$\Delta_D = \frac{D_s - D_E}{D_s} \times 100.$$

where

$\Delta l, \Delta h, \Delta b, \Delta d, \Delta D$ is the relative dimensional change, in %;

l_s, h_s, b_s is the test specimen length, thickness and width, before the heat treatment, in mm;


l_E, h_E, b_E is the test specimen length, thickness and width, after the heat treatment, in mm;

d_s, D_s is the test specimen diameter before the heat treatment, in mm;

d_E, D_E is the test specimen diameter after the heat treatment, in mm.


Table 14 — Test temperatures for determination of dimensional stability after heat treatment

Material	Test temperatures (°C)
PA 6	160
PA 6 C	160
PA 66	180
PA 12	140
PA 12 C	140
PA 46	200
PA 6/12 C	160
PBT	150
PC	130
PEEK	300
PET	160
POM	140
PPE + PS	110
PVDF	150

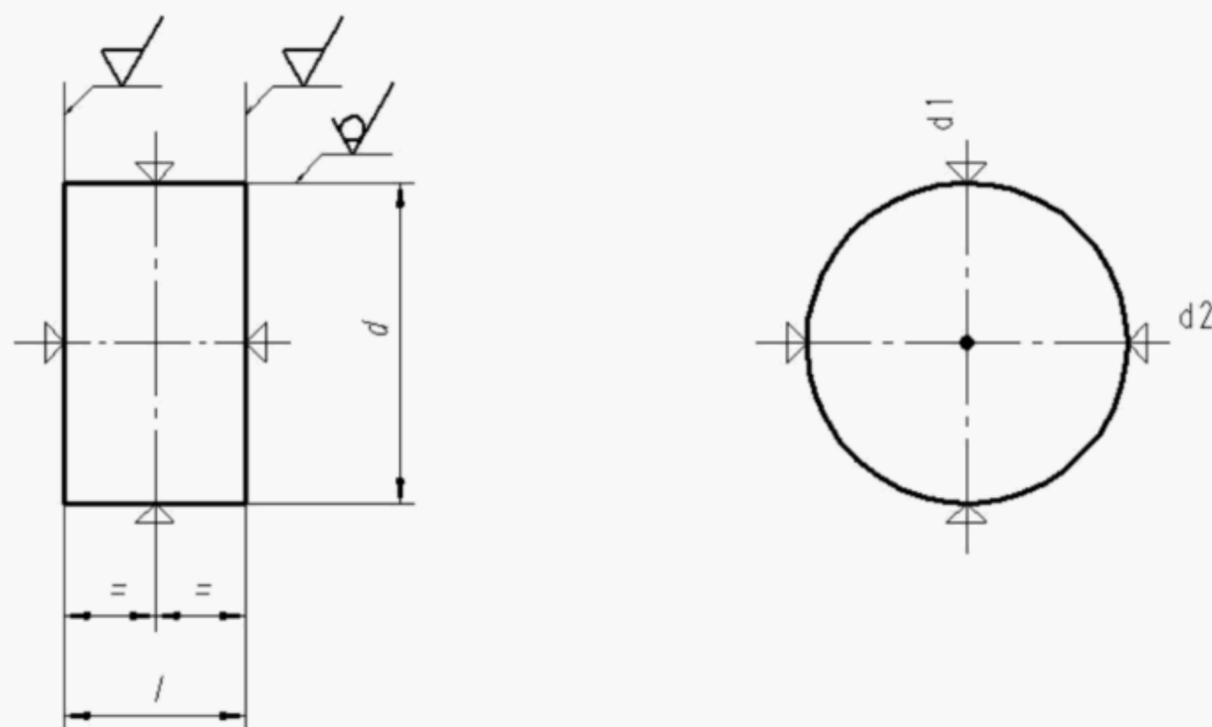


Key
d diameter of test specimens
l length of test specimens
▽ measuring points

Figure 9 — Measuring points on test specimens taken from rods

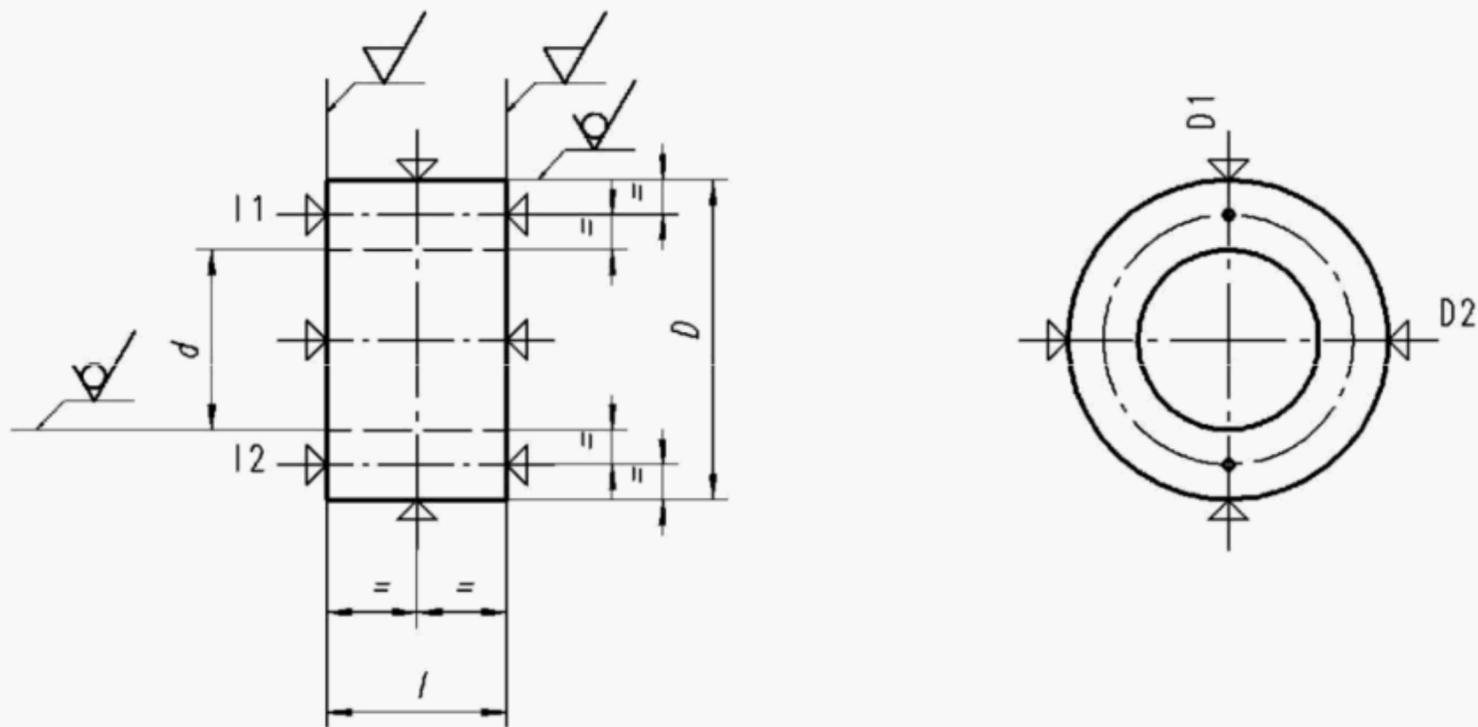

Key
 D outside diameter of test specimens
 d inside diameter of test specimens
 l length of test specimens
 ▽ measuring points

Figure 10 — Measuring points on test specimens taken from hollow bars

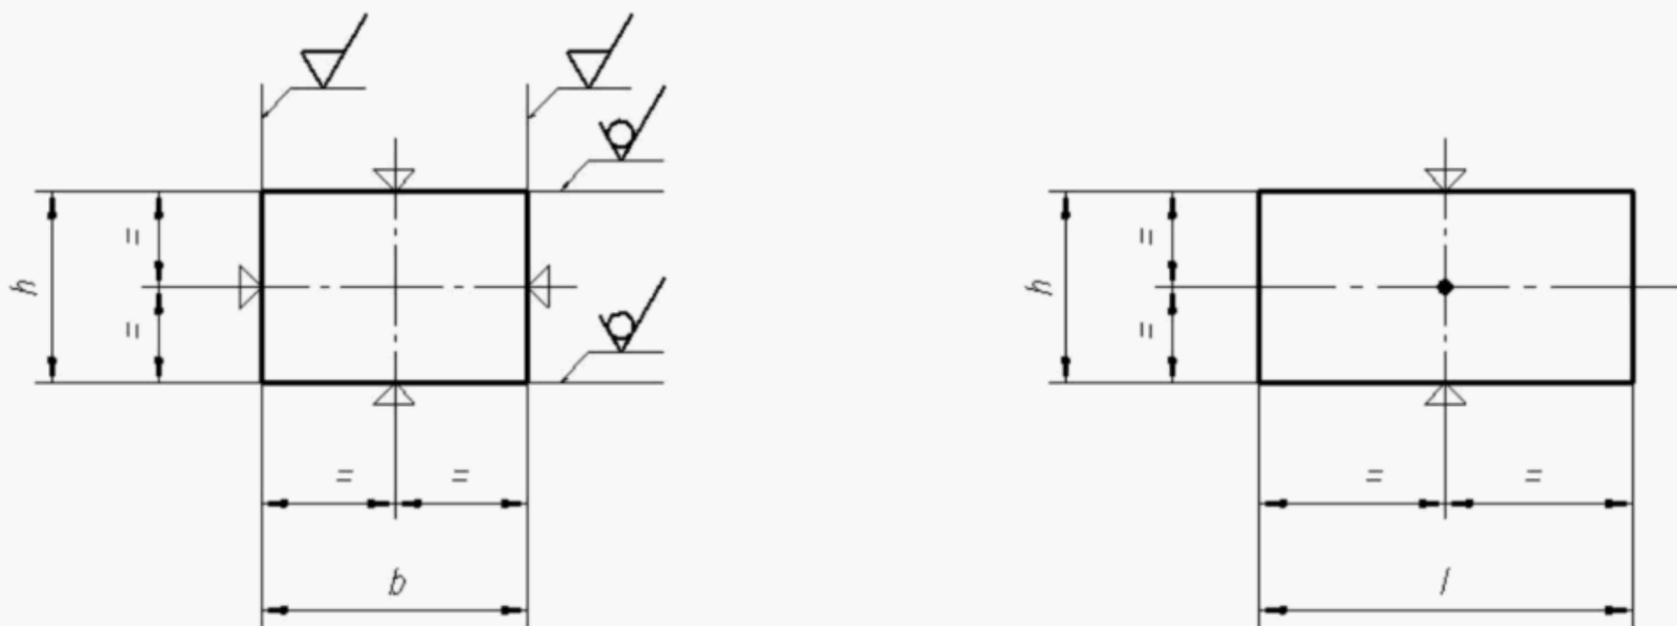

Key
 b width of test specimens (50 mm)
 l length of test specimens (60 mm)
 h thickness of test specimens
 ▽ measuring points

Figure 11 — Measuring points on test specimens taken from panels/plates

6.15 Preparation of test results

Unless otherwise stated in the test for the specific property, the average value of the individual test results shall be calculated and rated as a representative value for the property measured on the tested semi-finished product.

7 Designation

7.1 Rods

	Rod	EN 15860	PA 6	—	80	×	1000	—	natural
Form in which supplied	_____	_____	_____	_____	_____	_____	_____	_____	_____
Standard number	_____	_____	_____	_____	_____	_____	_____	_____	_____
Material	_____	_____	_____	_____	_____	_____	_____	_____	_____
Nominal diameter in millimetres	_____	_____	_____	_____	_____	_____	_____	_____	_____
Nominal length in millimetres	_____	_____	_____	_____	_____	_____	_____	_____	_____
Colour	_____	_____	_____	_____	_____	_____	_____	_____	_____

7.2 Hollow bars

	Hollow bar	EN 15860	POM-C	—	100	×	80	×	2000	—	natural
Form in which supplied	_____	_____	_____	_____	_____	_____	_____	_____	_____	_____	_____
Standard number	_____	_____	_____	_____	_____	_____	_____	_____	_____	_____	_____
Material	_____	_____	_____	_____	_____	_____	_____	_____	_____	_____	_____
Nominal outside diameter in millimetres	_____	_____	_____	_____	_____	_____	_____	_____	_____	_____	_____
Nominal inside diameter in millimetres	_____	_____	_____	_____	_____	_____	_____	_____	_____	_____	_____
Nominal length in millimetres	_____	_____	_____	_____	_____	_____	_____	_____	_____	_____	_____
Colour	_____	_____	_____	_____	_____	_____	_____	_____	_____	_____	_____

7.3 Panels/plates

	Panel/ plate	EN 15860	PC	—	20	×	500	×	3000	—	natural
Form in which supplied											
Standard number											
Material											
Nominal thickness in millimetres											
Nominal width in millimetres											
Nominal length in millimetres											
Colour											

8 Marking

Semi-finished products that meet the requirements of this standard can be marked as follows:

- a) manufacturer's mark;
- b) number of this European Standard (EN 15860);
- c) material designation;
- d) date of manufacture/production number.

Annex A (normative)

Procedure for the determination of microporosity in semi-finished products

Microporosity means microvoids which are visible to the naked eye when applying the dye penetration method described below.

For rods or hollow bars, a 100 mm long piece is cut in half lengthwise, approximately 2 mm off centre, and is then machined down to the centre so that a clean and smooth surface is obtained (surface roughness: $1,5 \mu\text{m} \leq Ra \leq 2,5 \mu\text{m}$) (see Figures A.1 and A.2).


For panels/plates, a 20 mm to 40 mm wide strip is cut over the full width of the panel/plate. Then, one face is machined over a depth of about 2 mm so that a clean and smooth surface is obtained (surface roughness: $1,5 \mu\text{m} \leq Ra \leq 2,5 \mu\text{m}$) (see Figure A.3).

After cleaning the machined surface, e. g. with isopropyl alcohol, the surface is coloured by means of a fluorescent permanent magic marker. Through capillary effect, the ink penetrates the pores, if present. After about one minute drying time, the coloured area is cleaned off with isopropyl alcohol. The ink or dye will not be washed from inside the pores and will show up as coloured particles (to be examined preferably using a UV-light sensor). If no coloured particles are visible, then the material does not have microporosity.

If coloured particles are visible, a measurement is made of the largest diameter (d' in case of rods) or the widest part (b' in case of hollow bars or panels) of the porosity line(s) over the 100 mm long piece (for rods or hollow bars) or over the full panel/plate width (B).

The value of the largest diameter or the widest part of the porosity line is then divided by the diameter of the rod or the wall thickness of the hollow bar or the thickness of the panel, and multiplied by 100 to obtain the percentage centreline porosity value. As indicated in 5.1, this value shall not exceed 4 %.


Dimensions in millimetres

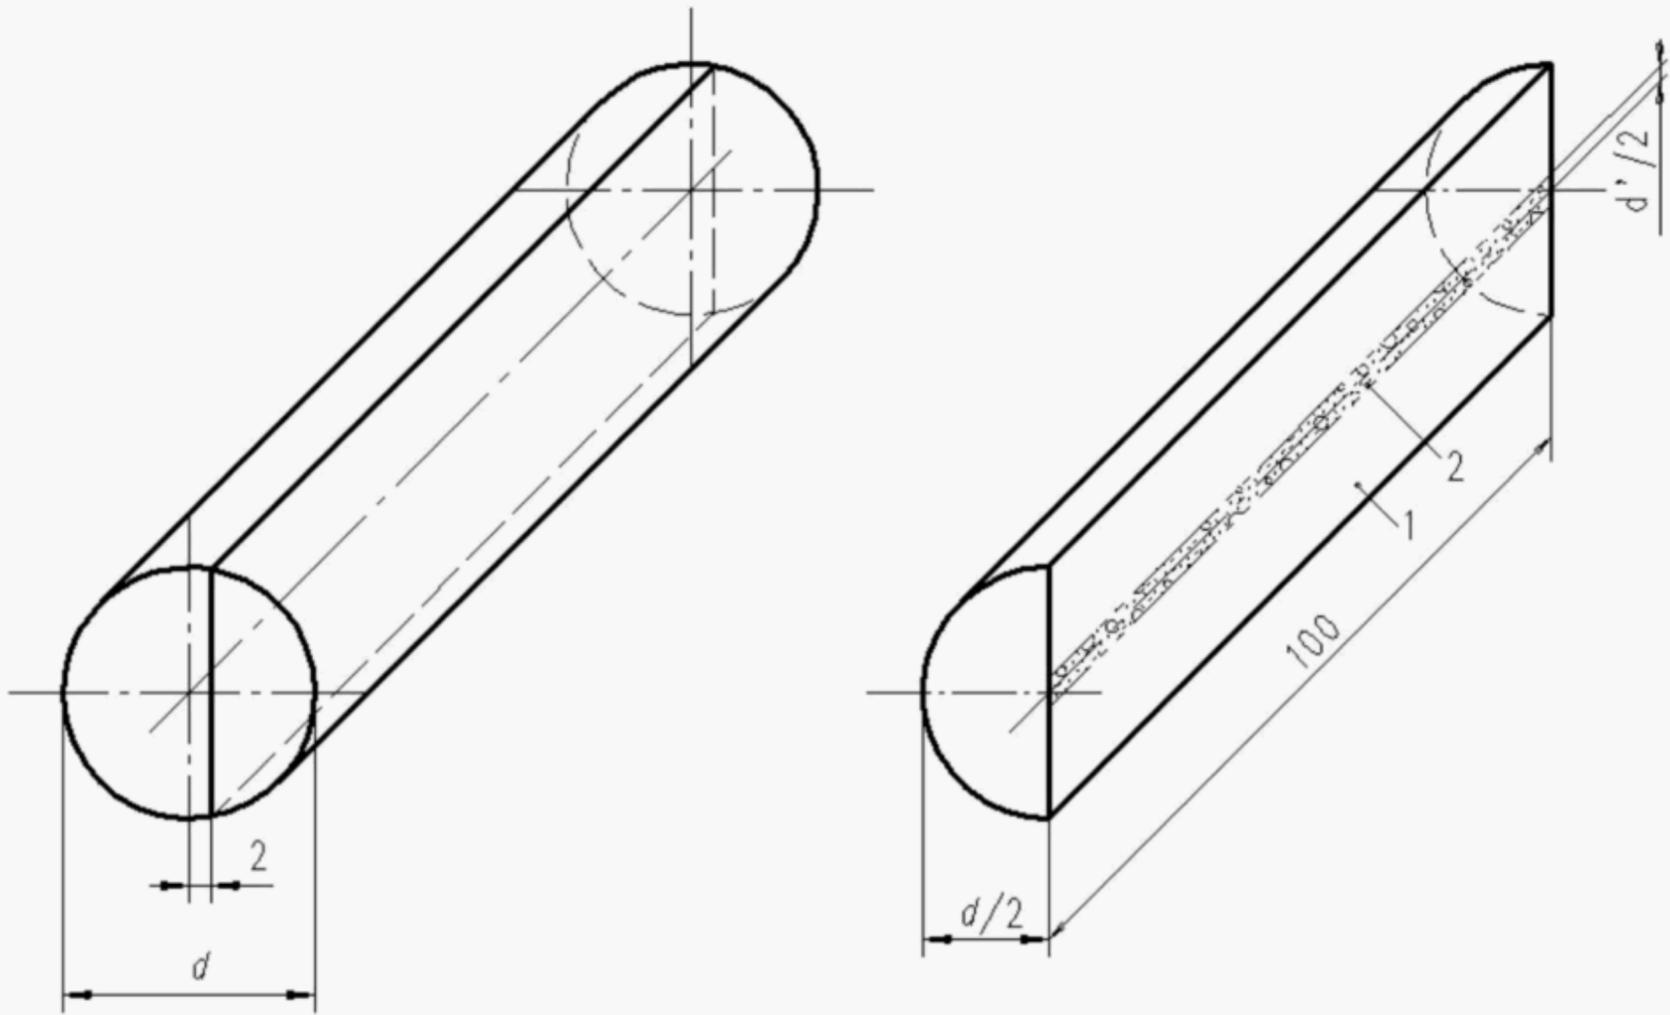

- Key
- 1 machined surface
 - 2 microporosity line
 - d diameter
 - d' maximum diameter of porosity line

Figure A.1 — Procedure for rods


Dimensions in millimetres

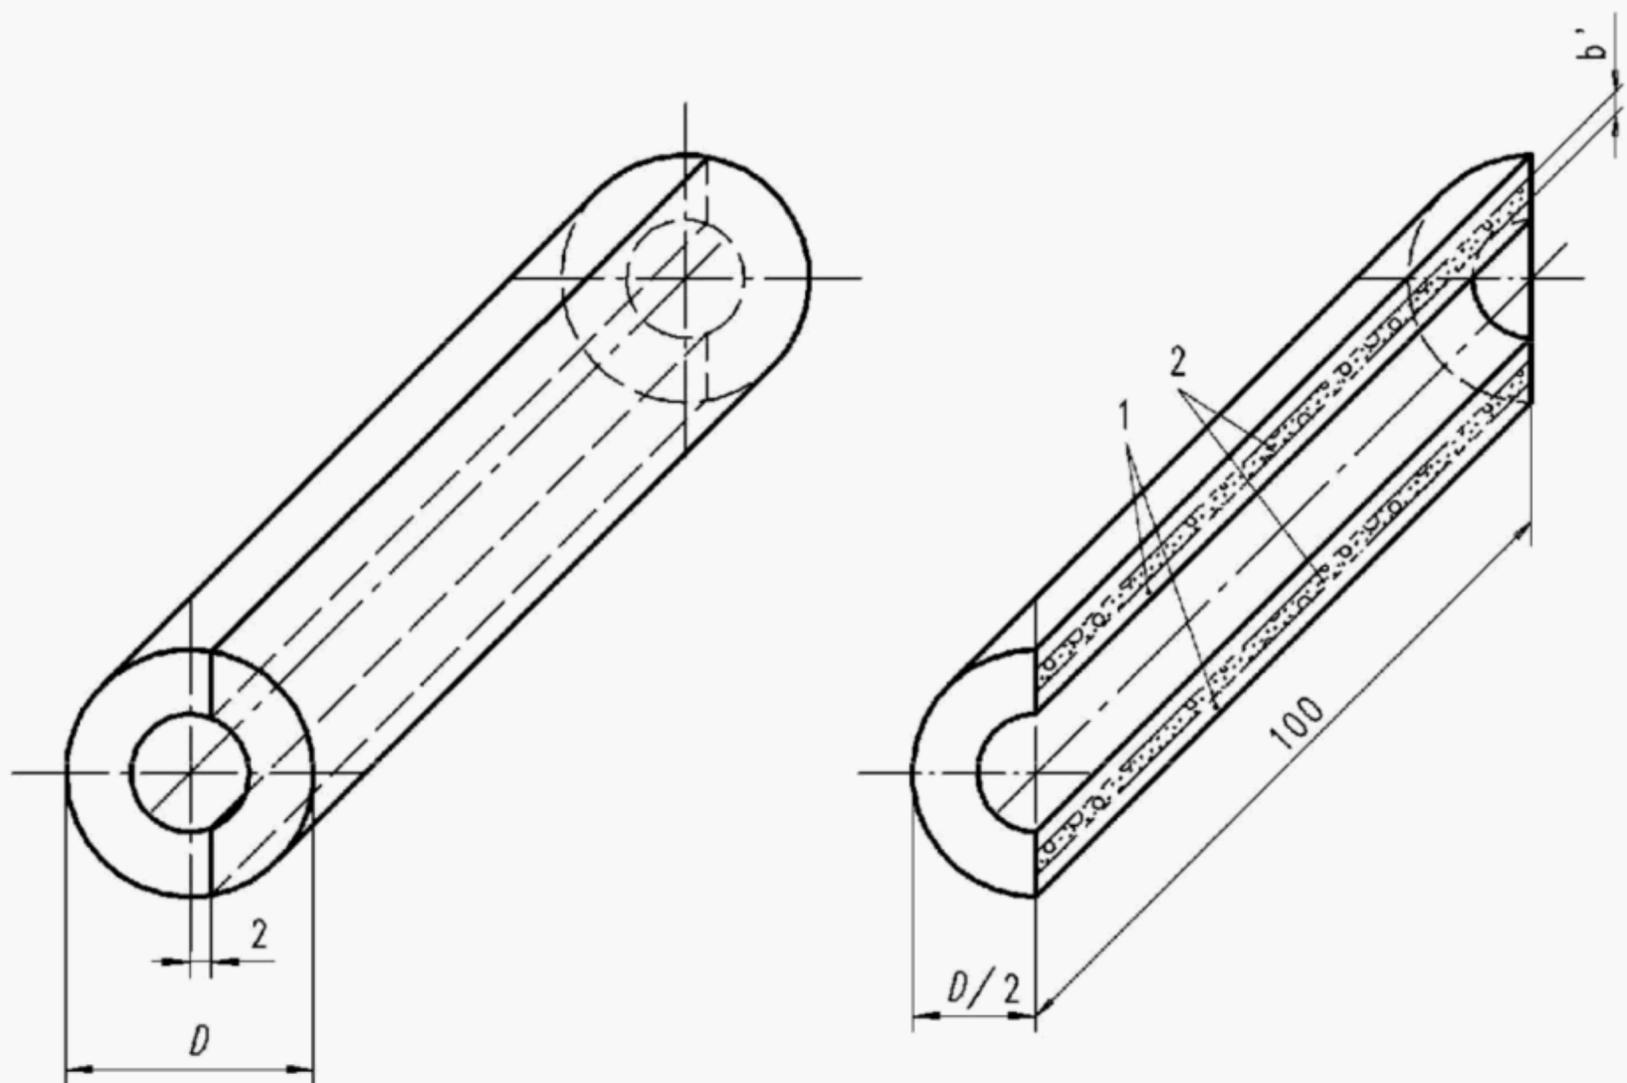

Key

- 1 machined surface
- 2 microporosity line
- D outside diameter
- b' maximum width of porosity line

Figure A.2 — Procedure for hollow bars

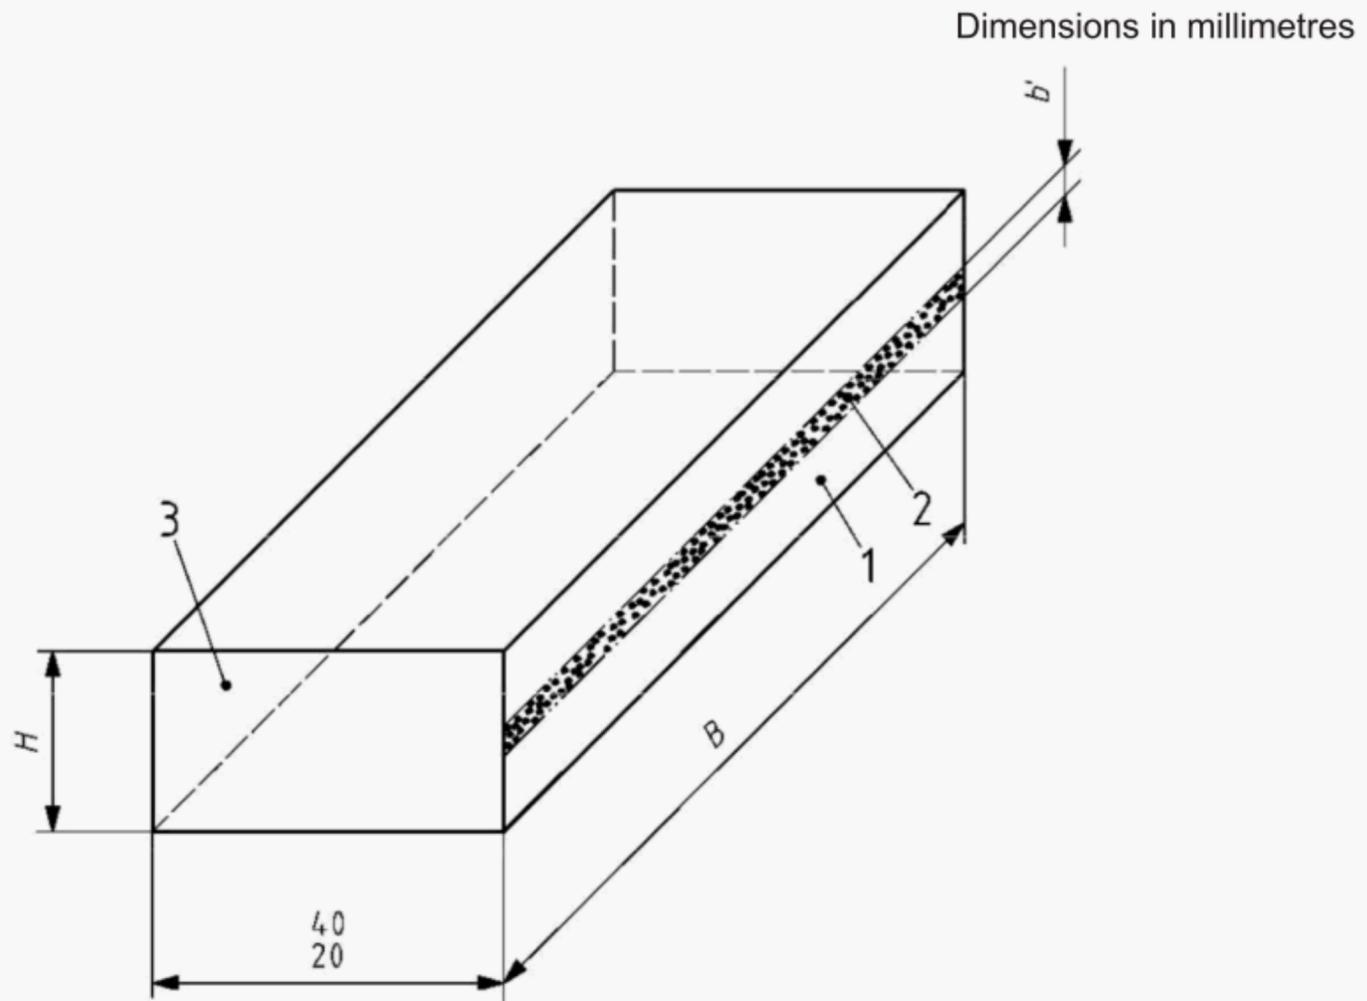

Key

- 1 machined surface
- 2 microporosity line
- 3 saw-cut surface

H thickness of panel

B width of panel

b' maximum width of porosity line

Figure A.3 — Procedure for panels/plates

Annex B (normative)

Tables for the conversion of deflection values (straightness)

Table B.1 — Conversion of the deflection f measured on a reference length of 1 000 mm to lengths of 300 mm to 3 000 mm

Dimensions in millimetres

Deflection f measured on a reference length of 1 000 mm	Deflection converted to lengths of 300 mm to 3 000 mm											
	300	400	500	600	700	800	900	1 000	1 250	1 500	2 000	3 000
1,50	0,13	0,24	0,37	0,54	0,73	0,96	1,21	1,50	2,34	3,38	6,00	13,50
2,50	0,22	0,40	0,62	0,90	1,22	1,60	2,02	2,50	3,91	5,63	10,00	22,50
3,00	0,27	0,48	0,75	1,08	1,47	1,92	2,43	3,00	4,69	6,75	12,00	27,01
3,50	0,31	0,56	0,87	1,26	1,71	2,24	2,83	3,50	5,47	7,88	14,00	31,51
4,00	0,36	0,64	1,00	1,44	1,96	2,56	3,24	4,00	6,25	9,00	16,00	36,02
5,00	0,45	0,80	1,25	1,80	2,45	3,20	4,05	5,00	7,81	11,25	20,01	45,04
6,50	0,58	1,04	1,62	2,34	3,18	4,16	5,26	6,50	10,16	14,63	26,01	58,58
7,50	0,67	1,20	1,87	2,70	3,67	4,80	6,07	7,50	11,72	16,88	30,02	67,62
8,00	0,72	1,28	2,00	2,88	3,92	5,12	6,48	8,00	12,50	18,01	32,02	72,15
10,00	0,90	1,60	2,50	3,60	4,90	6,40	8,10	10,00	15,63	22,51	40,05	90,29
12,50	1,12	2,00	3,12	4,50	6,12	8,00	10,12	12,50	19,54	28,15	50,09	113,07
15,00	1,35	2,40	3,75	5,40	7,35	9,60	12,15	15,00	23,45	33,79	60,16	135,99
17,50	1,57	2,80	4,37	6,30	8,57	11,20	14,17	17,50	27,36	39,44	70,26	159,08
20,00	1,80	3,20	4,99	7,19	9,79	12,79	16,20	20,00	31,28	45,09	80,39	182,37

NOTE 1 The deflection f is the maximum distance between the straight 1 000 mm long measuring ruler and the concave side of the semi-finished product

NOTE 2 Conversion calculation is based on the assumption that the deflection line is a circular function ($R^2 = X^2 + Y^2$).

Table B.2 — Conversion of the deflection *f* measured on lengths of 300 mm to 3 000 mm to a reference length of 1000 mm

Dimensions in millimetres					
300					
⇒ 1 000	400 ⇒ 1 000	500 ⇒ 1 000	600 ⇒ 1 000	700 ⇒ 1 000	800 ⇒ 1 000
0,15 ⇒ 1,67	0,25 ⇒ 1,56	0,40 ⇒ 1,60	0,55 ⇒ 1,53	0,75 ⇒ 1,53	1,00 ⇒ 1,56
0,25 ⇒ 2,78	0,40 ⇒ 2,50	0,60 ⇒ 2,40	0,90 ⇒ 2,50	1,20 ⇒ 2,45	1,60 ⇒ 2,50
0,35 ⇒ 3,89	0,55 ⇒ 3,44	0,85 ⇒ 3,40	1,20 ⇒ 3,33	1,60 ⇒ 3,27	2,20 ⇒ 3,44
0,45 ⇒ 5,00	0,70 ⇒ 4,38	1,10 ⇒ 4,40	1,60 ⇒ 4,44	2,25 ⇒ 4,59	3,00 ⇒ 4,69
0,55 ⇒ 6,11	0,90 ⇒ 5,63	1,40 ⇒ 5,60	2,00 ⇒ 5,56	2,80 ⇒ 5,71	3,75 ⇒ 5,86
0,65 ⇒ 7,22	1,10 ⇒ 6,88	1,75 ⇒ 7,00	2,50 ⇒ 6,95	3,50 ⇒ 7,14	4,50 ⇒ 7,03
0,75 ⇒ 8,34	1,30 ⇒ 8,13	2,00 ⇒ 8,00	3,00 ⇒ 8,33	4,00 ⇒ 8,16	5,25 ⇒ 8,20
0,85 ⇒ 9,45	1,50 ⇒ 9,38	2,30 ⇒ 9,20	3,50 ⇒ 9,72	4,50 ⇒ 9,19	6,00 ⇒ 9,38
1,00 ⇒ 11,12	1,75 ⇒ 10,94	2,75 ⇒ 11,00	4,00 ⇒ 11,11	5,50 ⇒ 11,23	7,00 ⇒ 10,94
1,20 ⇒ 13,34	2,10 ⇒ 13,13	3,25 ⇒ 13,01	4,75 ⇒ 13,20	6,50 ⇒ 13,27	8,50 ⇒ 13,28
1,40 ⇒ 15,57	2,50 ⇒ 15,64	3,75 ⇒ 15,01	5,50 ⇒ 15,29	7,50 ⇒ 15,31	10,00 ⇒ 15,63
1,60 ⇒ 17,80	2,90 ⇒ 18,15	4,50 ⇒ 18,02	6,50 ⇒ 18,07	9,00 ⇒ 18,38	11,50 ⇒ 17,98
1,90 ⇒ 21,15	3,40 ⇒ 21,28	5,25 ⇒ 21,03	7,50 ⇒ 20,86	10,50 ⇒ 21,45	13,50 ⇒ 21,11
2,20 ⇒ 24,50	3,80 ⇒ 23,80	6,00 ⇒ 24,04	8,50 ⇒ 23,64	11,50 ⇒ 23,50	15,00 ⇒ 23,46

Table B.2 (continued)

Dimensions in millimetres					
900					
⇒ 1 000	1250 ⇒ 1 000	1500 ⇒ 1 000	2000 ⇒ 1 000	2500 ⇒ 1 000	3000 ⇒ 1 000
1,25 ⇒ 1,54	2,40 ⇒ 1,54	3,50 ⇒ 1,56	6,00 ⇒ 1,50	9,50 ⇒ 1,52	14,00 ⇒ 1,56
2,00 ⇒ 2,47	4,00 ⇒ 2,56	5,50 ⇒ 2,44	10,00 ⇒ 2,50	16,00 ⇒ 2,56	23,00 ⇒ 2,56
2,75 ⇒ 3,40	5,50 ⇒ 3,52	8,00 ⇒ 3,56	14,00 ⇒ 3,50	22,00 ⇒ 3,52	32,00 ⇒ 3,55
3,50 ⇒ 4,32	7,25 ⇒ 4,64	10,50 ⇒ 4,67	18,00 ⇒ 4,50	29,00 ⇒ 4,64	42,00 ⇒ 4,66
4,25 ⇒ 5,25	9,00 ⇒ 5,76	13,00 ⇒ 5,78	23,00 ⇒ 5,75	36,00 ⇒ 5,76	52,00 ⇒ 5,77
5,50 ⇒ 6,79	10,50 ⇒ 6,72	15,50 ⇒ 6,89	27,50 ⇒ 6,87	43,00 ⇒ 6,87	62,00 ⇒ 6,88
6,50 ⇒ 8,03	12,50 ⇒ 8,00	18,00 ⇒ 8,00	32,50 ⇒ 8,12	50,00 ⇒ 7,99	72,00 ⇒ 7,98
8,00 ⇒ 9,88	15,00 ⇒ 9,60	22,00 ⇒ 9,77	38,50 ⇒ 9,61	61,00 ⇒ 9,74	88,00 ⇒ 9,75
9,50 ⇒ 11,73	18,00 ⇒ 11,52	26,00 ⇒ 11,55	46,00 ⇒ 11,48	72,00 ⇒ 11,49	105,00 ⇒ 11,62
11,00 ⇒ 13,58	21,50 ⇒ 13,75	31,00 ⇒ 13,76	54,00 ⇒ 13,47	84,00 ⇒ 13,39	120,00 ⇒ 13,26
12,50 ⇒ 15,43	25,00 ⇒ 15,99	36,00 ⇒ 15,98	63,00 ⇒ 15,70	99,00 ⇒ 15,76	145,00 ⇒ 15,98
14,50 ⇒ 17,91	28,50 ⇒ 18,23	41,00 ⇒ 18,19	73,00 ⇒ 18,18	115,00 ⇒ 18,27	165,00 ⇒ 18,14
17,00 ⇒ 20,99	32,50 ⇒ 20,78	47,00 ⇒ 20,84	84,00 ⇒ 20,89	135,00 ⇒ 21,39	195,00 ⇒ 21,35
19,00 ⇒ 23,47	37,00 ⇒ 23,65	54,00 ⇒ 23,93	96,00 ⇒ 23,83	150,00 ⇒ 23,71	220,00 ⇒ 23,98

NOTE 1 The deflection *f* is the maximum distance between the straight 1 000 mm long measuring ruler and the concave side of the semi-finished product

NOTE 2 Conversion calculation is based on the assumption that the deflection line is a circular function ($R^2 = X^2 + Y^2$).

– example 1:

A rod (\varnothing 60 mm \times 3 000 mm) made from fibre-reinforced PEEK is laid unconstrained on its side on a flat surface. By means of a straight, 1 000 mm long measuring ruler, the maximum deviation from the straight line over the full 3 000 mm rod length is measured: $f = 3$ mm. According to Column 1 of Table 3, this deviation is acceptable ($\leq 5,0$ mm).

If the maximum deviation from the straight line is measured on the same rod using a 500 mm or 2 000 mm long measuring ruler, then a deflection f of 0,75 mm or 12 mm would be found, as can be derived from Table B.1.

– example 2:

A panel (30 mm \times 600 mm \times 3 000 mm) made from PET is laid unconstrained on a flat surface with its crown side down. By means of a straight, 1 000 mm long measuring ruler, the maximum deviations from the straight line along different directions are measured (see Figures 4a), 4b) and 4c)).

The maximum deviation from the straight line over the full 3 000 mm panel length is: $f_1 = 2$ mm. According to Table 8, this deviation is acceptable ($\leq 2,0$ mm).

The maximum deviation from the straight line over the 600 mm panel width (measured at different positions over the 3 000 mm panel length) is $f_2 = 2$ mm. Using Table B.2, this value corresponds to a deflection of 5,56 mm over a reference length of 1 000 mm. According to Table 8, this deviation is not acceptable ($> 3,5$ mm)

Measured along the lengthwise edges of the panel, the maximum deviation from the straight line over the full 3 000 mm panel length is $f_3 = 2$ mm. According to Table 8, this deviation is acceptable ($\leq 4,0$ mm).

Annex C (informative)

Examples of calculation of dimensional stability after heat treatment

C.1 Rods

Three test specimens of length ($25 \pm 0,1$) mm are fabricated from a PET rod (\varnothing 120 mm) as described in 6.3.4.1. After being machined and having reached adequate temperature equilibrium in the standard atmosphere at (23 ± 2) °C, the length (l) and diameter (d) of each test specimen are measured to the nearest 0,01 mm – as described in 6.14.

The test specimens are then subjected to the heat treatment described in 6.14 in an oven with forced air circulation, using a test temperature of 160 °C (see Table 14).

Then, after temperature equilibrium has been reached for 12 h in the standard atmosphere at (23 ± 2) °C, the length (l) and diameter (d) of the test specimens are measured again to the nearest 0,01 mm and at the same positions as during the first measurements

Table C.1 — Calculation of dimensional stability for rods after heat treatment

Dimensions	Measured values of the different dimensions before and after heat treatment						Relative changes as average values			of the three test specimens ^a					
	Test specimen 1			Test specimen 2			Test								
	Before						After	Relative	Before		After	Relative			
	mm						mm	%	mm		mm	%	mm	mm	%
d1	122,15	121,95	- 0,16	122,22	122,04	- 0,15	122,24	122,01	- 0,19						
d2	122,35	122,10	- 0,20	122,01	121,78	- 0,19	121,95	121,74	- 0,17						
		$d_{\text{average}} \Rightarrow$	- 0,18		$d_{\text{average}} \Rightarrow$	- 0,17		$d_{\text{average}} \Rightarrow$	- 0,18						
l	25,05	24,80	- 1,00	25,10	24,82	- 1,12	24,94	24,67	- 0,18						
	A			B			C			D = (A+B+C)/3					

^a These values shall be evaluated compared with the guideline values given in Table 11

C.2 Hollow bars

Three test specimens of length ($25 \pm 0,1$ mm) are fabricated from a (\varnothing 180 mm × \varnothing 140 mm) POM-C hollow bar as described in 6.3.4.1. After being machined and having reached adequate temperature equilibrium in the standard atmosphere at (23 ± 2) °C, the length (l) and outside diameter (D) of each test specimen are measured to the nearest 0,01 mm – as described in 6.14.

The test specimens are then subjected to the heat treatment described in 6.14 in an oven with forced air circulation, using a test temperature of 140 °C (see Table 14).

Then after temperature equilibrium has been reached for 12 h in the standard atmosphere at (23 ± 2) °C, the length (l) and outside diameter (D) of the three test specimens are measured again to the nearest 0,01 mm and at the same positions as during the first measurements

Table C.2 — Calculation of dimensional stability for hollow bars after heat treatment

Dimensions	Measured values of the different dimensions before and after heat treatment									Relative changes as average values of the three test specimens ^a
	Test specimen 1			Test specimen 2			Test specimen 3			
	Before	After	Relative change	Before	After	Relative change	Before	After	Relative change	
	mm	mm	%	mm	mm	%	mm	mm	%	
D ₁	183,80	183,69	- 0,06	183,75	183,62	- 0,07	183,68	183,60	- 0,04	- 0,05
D ₂	183,35	183,27	- 0,04	183,40	183,30	- 0,05	183,28	183,21	- 0,04	
	D _{average} ⇒		- 0,05	D _{average} ⇒		- 0,06	D _{average} ⇒		- 0,04	
h ₁	25,10	25,02	- 0,32	24,94	24,85	- 0,36	25,05	24,98	- 0,28	- 0,31
h ₂	25,08	25,01	- 0,28	24,96	24,88	- 0,32	25,03	24,95	- 0,32	
	l _{average} ⇒		- 0,30	l _{average} ⇒		- 0,34	l _{average} ⇒		- 0,30	
	A			B			C			D = (A+B+C)/3

^a These values shall be evaluated compared with the guideline values given in Table 11.

C.3 Panels/plates

Three rectangular test specimens (50 ± 0,2) mm × (60 ± 1) mm are fabricated – as described in 6.3.4.2 and shown in Figure 8 – from a 40 mm thick and 600 mm wide PA 66 panel. After being machined and having reached adequate temperature equilibrium in the standard atmosphere (23 ± 2) °C, width (b) and thickness (h) of each test specimen are measured to the nearest 0,01 mm – as described in 6.14.

The test specimens are then subjected to the heat treatment described in 6.14 in an oven with forced air circulation, using a test temperature of 180 °C (see Table 14).

Then, after temperature equilibrium has been reached for 12 h in the standard atmosphere at (23 ± 2) °C, the width (b) and thickness (h) of the three test specimens are measured again to the nearest 0,01 mm and at the same positions as during the first measurements

Dimensions	Table C.3 — Calculation of dimensional stability for panels/plates after heat treatment									Relative changes as average values of the three test specimens ^a
	Measured values of the different dimensions before and after heat treatment									
	Test specimen 1			Test specimen 2			Test specimen 3			
	Before	After	Relative change	Before	After	Relative change	Before	After	Relative change	
	mm	mm	%	mm	mm	%	mm	mm	%	%
b	50,16	49,75	- 0,82	49,96	49,58	- 0,76	50,06	49,66	- 0,80	- 0,79
h	41,40	41,66	0,63	41,50	41,74	0,58	41,36	41,64	0,68	0,63
	A			B			C			D = (A+B+C)/3

^a These values shall be evaluated compared with the guideline values given in Table 11.

Bibliography

- [1] EN ISO 1163-1, Plastics — Unplasticized poly(vinyl chloride) (PVC-U) moulding and extrusion materials — Part 1: Designation system and basis for specifications (ISO 1163-1:1995)
- [2] EN ISO 1872-1, Plastics — Polyethylene (PE) moulding and extrusion materials — Part 1: Designation system and basis for specifications (ISO 1872-1:1993)
- [3] EN ISO 1873-1, Plastics — Polypropylene (PP) moulding and extrusion materials — Part 1: Designation system and basis for specifications (ISO 1873-1:1995)
- [4] EN ISO 1874-1, Plastics — Polyamide (PA) moulding and extrusion materials — Part 1: Designation (ISO 1874-1:1992)
- [5] EN ISO 2580-1, Plastics — Acrylonitrile-butadiene-styrene (ABS) moulding and extrusion materials — Part 1: Designation system and basis for specifications (ISO 2580-1:2002)
- [6] EN ISO 7391-1, Plastics — Polycarbonate (PC) moulding and extrusion materials — Part 1: Designation system and basis for specifications (ISO 7391-1:2006)
- [7] EN ISO 7792-1, Plastics — Thermoplastic polyester (TP) moulding and extrusion materials — Part 1: Designation system and basis for specifications (ISO 7792-1:1997)
- [8] EN ISO 9988-1, Plastics — Polyoxymethylene (POM) moulding and extrusion materials — Part 1: Designation system and basis for specifications (ISO 9988-1:2004)
- [9] EN ISO 11542-1, Plastics — Ultra-high-molecular-weight polyethylene (PE-UHMW) moulding and extrusion materials — Part 1: Designation system and basis for specifications (ISO 11542-1:2001)
- [10] EN ISO 11963, Plastics — Polycarbonate sheets — Types, dimensions and characteristics (ISO 11963:1995)
- [11] EN ISO 12086-1, Plastics — Fluoropolymer dispersions and moulding and extrusion materials — Part 1: Designation system and basis for specifications (ISO 12086-1:2006)
- [12] EN ISO 15103-1, Plastics — Poly(phenylene ether) (PPE) moulding and extrusion materials — Part 1: Designation system and basis for specifications (ISO 15103-1:2000)
- [13] ISO 15104, Plastics — Extruded sheets of poly(vinylidene fluoride) (PVDF) — Requirements and test methods

112

This page deliberately left blank

British Standards Institution (BSI)

BSI is the independent national body responsible for preparing British Standards and other standards-related publications, information and services.

It presents the UK view on standards in Europe and at the international level.

It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover.

Tel: +44 (0)20 8996 9001 Fax: +44 (0)20 8996 7001

BSI offers Members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Tel: +44 (0)20 8996 7669 Fax: +44 (0)20 8996 7001
Email: plus@bsigroup.com

Buying standards

You may buy PDF and hard copy versions of standards directly using a credit card from the BSI Shop on the website www.bsigroup.com/shop. In addition all orders for BSI, international and foreign standards publications can be addressed to BSI Customer Services.

Tel: +44 (0)20 8996 9001 Fax: +44 (0)20 8996 7001
Email: orders@bsigroup.com

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Knowledge Centre.
Tel: +44 (0)20 8996 7004 Fax: +44 (0)20 8996 7005
Email: knowledgecentre@bsigroup.com

Various BSI electronic information services are also available which give details on all its products and services.

Tel: +44 (0)20 8996 7111 Fax: +44 (0)20 8996 7048
Email: info@bsigroup.com

BSI Subscribing Members are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration.

Tel: +44 (0)20 8996 7002 Fax: +44 (0)20 8996 7001
Email: membership@bsigroup.com

Information regarding online access to British Standards via British Standards Online can be found at www.bsigroup.com/BSOL

Further information about BSI is available on the BSI website at www.bsigroup.com/standards

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies.

Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. This does not preclude the free use, in the course of implementing the standard of necessary details such as symbols, and size, type or grade designations. If these details are to be used

for any other purpose than implementation then the prior written permission of BSI must be obtained. Details and advice can be obtained from the Copyright & Licensing Manager.

Tel: +44 (0)20 8996 7070
Email: copyright@bsigroup.com

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Tel +44 (0)20 8996 9001
Fax +44 (0)20 8996 7001
www.bsigroup.com/standards



raising standards worldwide™

Provided by IHS
No reproduction or networking permitted without license from IHS

Not for Resale