



BSI Standards Publication

Machinery for forestry — Glazing and panel materials used in operator enclosures for protection against thrown sawteeth — Test method and performance criteria

NO COPYING WITHOUT BSI PERMISSION EXCEPT AS PERMITTED BY COPYRIGHT LAW

National foreword

This British Standard is the UK implementation of ISO 11839:2010.

The UK participation in its preparation was entrusted to Technical Committee AGE/29, Forestry machinery.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© BSI 2010

ISBN 978 0 580 65598 2

ICS 65.060.80

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 October 2010.

Amendments issued since publication

Date	Text affected
<hr/>	

INTERNATIONAL STANDARD

BS ISO 11839:2010

ISO
11839

First edition
2010-10-01

Machinery for forestry — Glazing and panel materials used in operator enclosures for protection against thrown sawteeth — Test method and performance criteria

*Matériel forestier — Matériaux pour vitrage et panneaux utilisés dans
l'enceinte de l'opérateur contre la projection des dents de scie —
Méthode d'essai et critères de performance*



Reference number
ISO 11839:2010(E)

© ISO 2010

PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.



COPYRIGHT PROTECTED DOCUMENT

© ISO 2010

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 11839 was prepared by Technical Committee ISO/TC 23, *Tractors and machinery for agriculture and forestry*, Subcommittee SC 15, *Machinery for forestry*.

Introduction

Forestry machines that use circular saws with replaceable sawteeth can expose the operator to the hazard of thrown sawteeth. Operator enclosures on forestry machinery provide protection from a variety of hazards by interposing a system of structural members and panel materials between the operator and potential hazards (see, for example, ISO 8083 for falling objects or ISO 8084 for poking hazards).

When there is a hazard from circular-saw thrown sawteeth, panel and glazing materials used in operator enclosures can be appropriately selected to provide operator protection based upon this International Standard. Although surfaces meeting the criteria given in this International Standard might not give protection under all conceivable circumstances in which the machine could be impacted by thrown sawteeth, it is expected that protection against sawteeth thrown from circular saws will be provided under normal operating conditions.

Machinery for forestry — Glazing and panel materials used in operator enclosures for protection against thrown sawteeth — Test method and performance criteria

CAUTION — Some of the tests specified in this International Standard involve the use of processes which could lead to a hazardous situation.

1 Scope

This International Standard specifies test procedures and performance requirements for determining the protective ability of panel materials used in forestry-machinery operator enclosures intended to protect the operator against sawteeth thrown by circular-saw components. This particular type of hazard is specifically defined by the size and velocity of the sawteeth and is unique to these cutting devices.

This International Standard is applicable to panel materials for forestry machines defined in ISO 6814 that include an integrated or attached circular sawing device, controlled or powered by the primary machine (e.g. topping saws, felling saws or bucking saws).

It does not address protection from chain-shot hazards (see ISO 11837).

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 6814, *Machinery for forestry — Mobile and self-propelled machinery — Terms, definitions and classification*

3 Tests

3.1 Test equipment

3.1.1 Projectile launcher, capable of propelling the specified test projectiles at the required velocities. The launcher shall have a controllable means of adjusting velocity. The launcher shall also have a means of orienting and directing the test projectile in relatively linear motion with the cutting surface towards the target. The test projectile may be supported in the launcher by a test projectile holder (i.e. a sabot). Such a test projectile holder should be less than 10 % of the mass of the tooth projectile being propelled, and any impact of the holder on the test panel shall be clearly inconsequential to the test result (see Figure 1).

3.1.2 Test projectile (F1), consisting of a representative four-pointed sawtooth, $300\text{ g} \pm 5\text{ g}$, with a cutting surface $50\text{ mm} \pm 1\text{ mm}$ square (see Figure 2).

3.1.3 Test projectile (F2), consisting of a representative, four-pointed sawtooth, $800\text{ g} \pm 5\text{ g}$, with a cutting surface $60\text{ mm} \pm 1\text{ mm}$ square (see Figure 2).

3.1.4 Target panel opening, consisting of a rigid steel frame surrounding a square opening of $450\text{ mm} \pm 1\text{ mm} \times 450\text{ mm} \pm 1\text{ mm}$.

3.1.5 Corrugated cardboard indicator panel, $500\text{ mm} \times 500\text{ mm}$, positioned $250\text{ mm} \pm 5\text{ mm}$ directly behind the target panel opening.

3.1.6 Target support structure that rigidly positions the target assembly perpendicular to the line of motion of the test projectile, with the target surface $3\,000\text{ mm} \pm 50\text{ mm}$ from the muzzle of the launcher.

3.1.7 Means of measuring test projectile velocity to an accuracy of $\pm 2\text{ m/s}$.

3.1.8 Means of measuring panel surface temperature to an accuracy of $\pm 1\text{ }^{\circ}\text{C}$.

3.1.9 Containment structure surrounding the test projectile line of motion, target assembly and indicator panel to provide suitable protection for test personnel.

3.2 Test samples and mounting

3.2.1 Test samples shall be representative of the commercial specification of the given product material. Appropriate material properties shall be determined and reported to verify test conditions.

3.2.2 Test samples shall be mounted onto the target panel opening using the manufacturer's specified attachment methods. The exception to this are test samples from materials that are typically attached using permanent methods such as welding; these may be attached to a separate frame that is then bolted to the target panel opening. Mounting details shall be recorded and reported.

3.3 Test method

3.3.1 Five samples shall be tested at low temperature and five samples at room temperature. Each sample shall be impacted once. The low-temperature samples shall be conditioned for 3 h prior to testing with the impact side exposed to $-32\text{ }^{\circ}\text{C} \pm 3\text{ }^{\circ}\text{C}$, and the operator side shall be exposed to a room temperature of $+22\text{ }^{\circ}\text{C} \pm 3\text{ }^{\circ}\text{C}$. The room temperature samples shall be conditioned for 3 h at $+22\text{ }^{\circ}\text{C} \pm 3\text{ }^{\circ}\text{C}$.

3.3.2 Five samples of non-metallic materials shall also be high-temperature-tested at $+49\text{ }^{\circ}\text{C} \pm 3\text{ }^{\circ}\text{C}$. Samples shall be conditioned at the elevated temperature for a minimum of 3 h prior to testing.

3.3.3 Each material shall be tested at the appropriate energy level, namely either

- 1 084 J to 1 311 J for F1, or
- 4 840 J to 5 856 J for F2.

The selection of the energy level shall be based on consideration of the type of thrown sawteeth hazard the material will face, in accordance with Annex B.

3.3.4 The F1 test projectile shall impact the target at a velocity of 85 m/s to 94 m/s. The F2 test projectile shall impact the target at a velocity of 110 m/s to 121 m/s.

3.3.5 If the velocity of the test projectile is less than the minimum specified velocity and the sample does not fail, the test shall be repeated. If the velocity of the test projectile is less than the minimum velocity and the sample fails, the test result (failure) is accepted. If the velocity of the test projectile is more than the maximum velocity, and the test sample passes, the test result (pass) is considered acceptable.

3.3.6 The test projectile shall impact the panel with the cutting surface forward in at least three of the sample impacts and within the target opening.


4 Performance requirements

The panel material is deemed to have failed if the test projectile and/or panel fragments impact the indicator panel. All samples shall pass the test in order for the material to be classified at the tested level.

5 Reporting results

The results of the tests shall be reported using a test report whose content is in accordance with Annex A.

Dimensions in millimetres

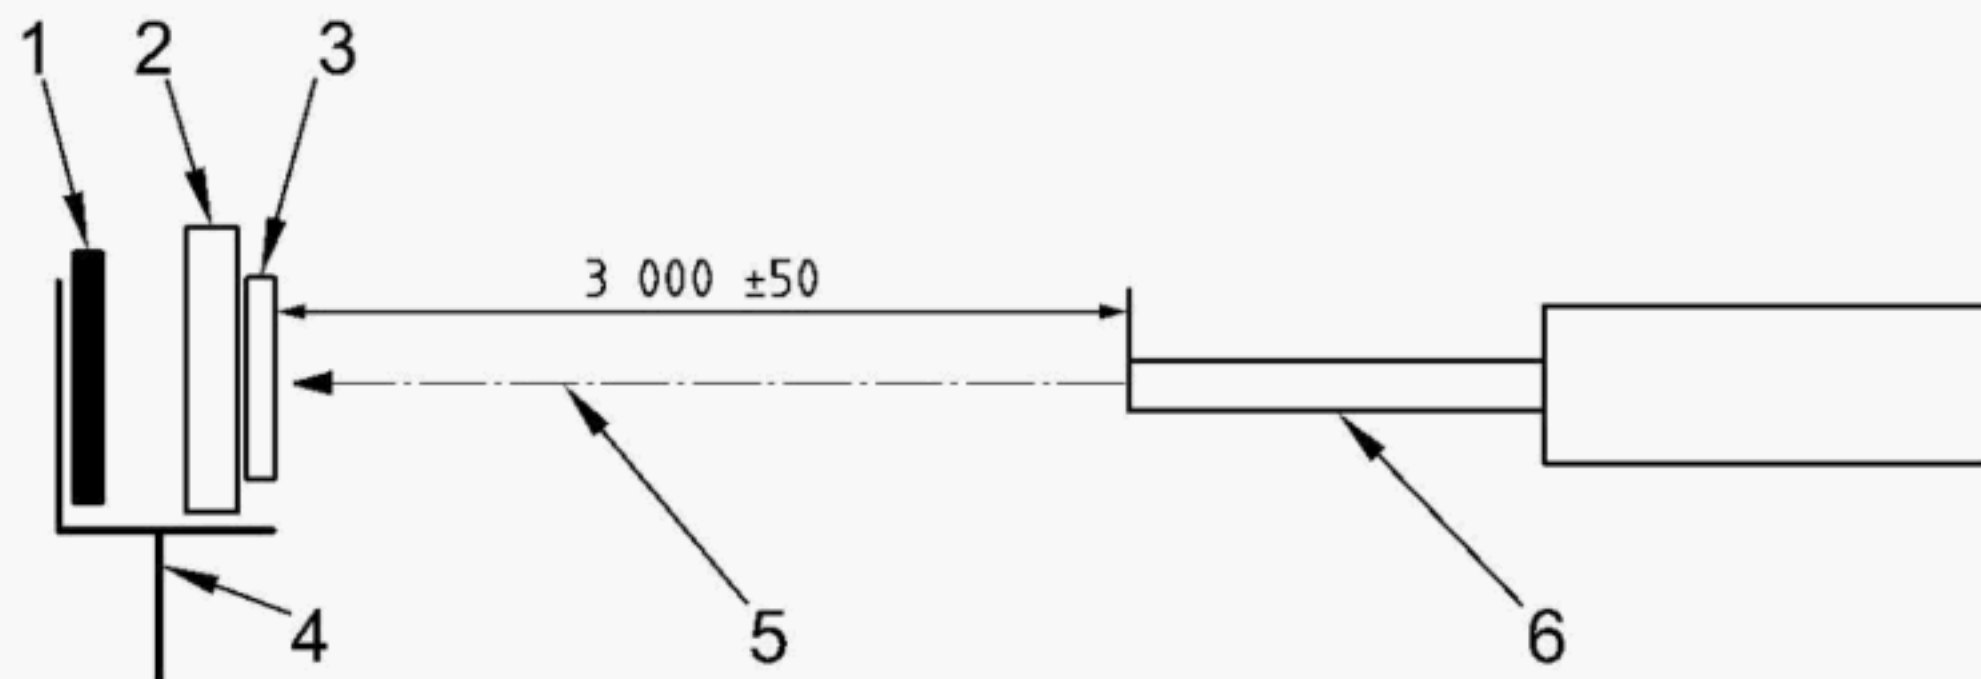

Key

- 1 indicator panel
- 2 target panel opening
- 3 target panel
- 4 target support structure
- 5 line of motion
- 6 projectile launcher

Figure 1 — Illustrative arrangement of test equipment

Dimensions in millimetres

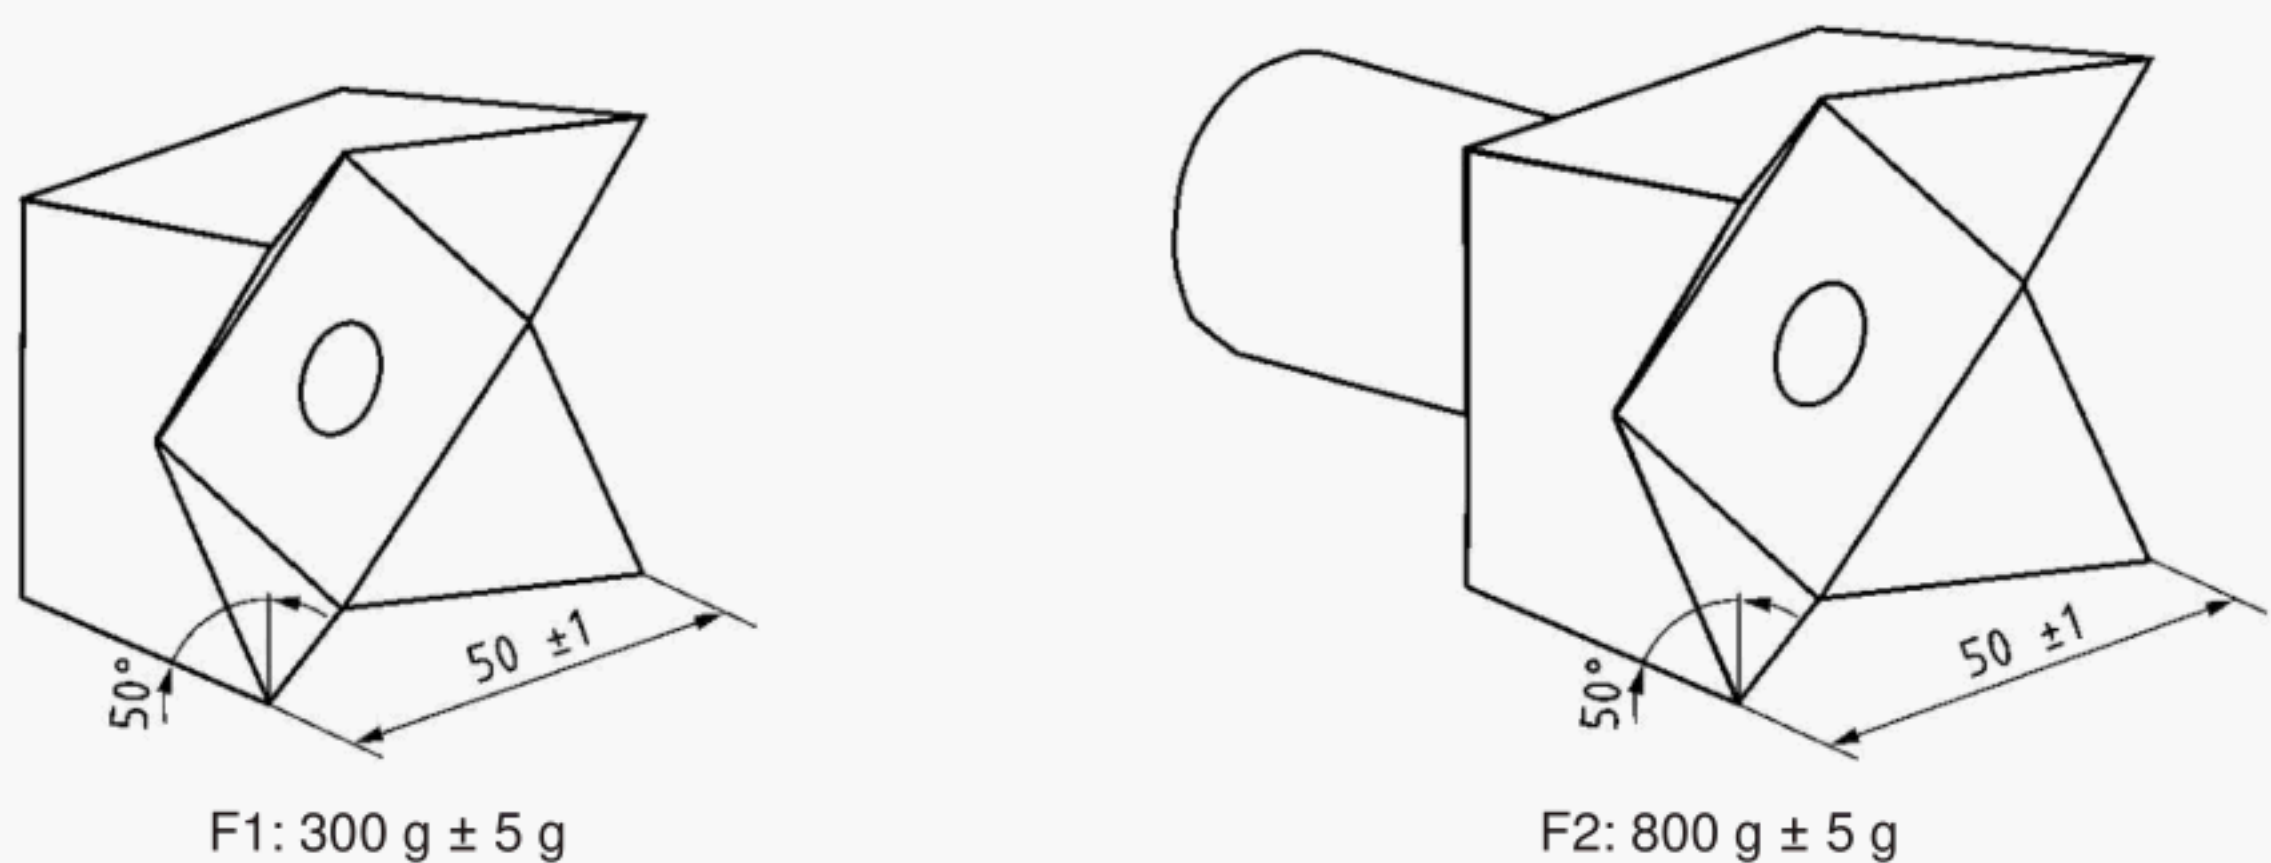


Figure 2 — Illustrative test projectile specification

Annex A (normative)

Test report

A.1 Material description

Manufacturer

Dimensions (thickness)

Construction (layers, coatings, etc.)

Material compound

Source information, lot number, manufacturing date

Glazing attachment method

A.2 Test conditions

Sample/test number

Temperature of material

Test projectile mass

Actual test projectile velocity at impact

Orientation of test projectile at impact

A.3 Test summary

Number of samples tested at each temperature condition:

..... /-32 °C, /+22 °C, /+49 °C (for non-metallic only)

Number of samples passing the test at each temperature condition:

..... /-32 °C, /+22 °C, /+49 °C (for non-metallic only)

A.4 Test results

The velocity of the test projectile met/did not meet the specified criteria (see 3.3.4).

The material failed/did not fail under impact (see Clause 4).

Therefore, the test result is acceptable/not acceptable according to the requirements of this International Standard (see Clause 4), and the material tested passed/did not pass.

Date of test

Name and address of test facility

Name of test engineer

Date and number of test report

Annex B (normative)

Thrown sawteeth hazard from circular saws

One means of cutting trees is the circular saw, a rotating disk with peripherally-mounted teeth. There are two basic types of circular saw: intermittent saws, where the saw only rotates when it is powered through a tree; and continuous saws, where the saw rotates all the time. Intermittent saws tend to have lower-speed, higher-torque designs, while continuous saws have high speeds and lower torque. The inertia stored in the high-speed saw disk is a key factor in maintaining rotation during a cut. Continuous saw disks also tend to have larger diameter than intermittent disks. It is generally assumed that the thrown sawteeth hazard is associated with the continuous saw design where the tip speed is highest and the possibility for unguarded blade contact is greater.

A survey of high-speed sawhead specifications identified over 40 models in current production. Older designs are still in use, but specifications were unavailable. Most of the designs (68 %) rotated at a speed of $1\,300\text{ min}^{-1}$ or greater, although the rotational speeds ranged from 600 min^{-1} to $1\,650\text{ min}^{-1}$. Combining rotation with disk diameter to calculate tip speed reveals a narrower distribution, with almost all designs (88 %) working at a tip speed that exceeded 85 m/s. The highest tip speed in the sampled designs was 102 m/s.

There is very little published information about the actual failure modes of the circular sawteeth. Anecdotal reports suggest that loosening mounting bolts can lead to detachment. Operators have reported missing teeth in trade safety reports. For the purposes of this International Standard, it is assumed that, if a mounting bolt fails, the tooth would separate from the holder and be carried in the debris stream around the inside of the saw shroud. At the discharge point, the tooth could be moving at the tip speed velocity. The performance test is structured around the assumption of straight-line motion at tip speed. However, there may be other failure modes that could produce higher sawteeth velocities in field conditions.

Just as there is a wide range of sawhead designs, there is a wide range of sawteeth and mounting configurations. Teeth generally have multiple cutting faces that allow for repositioning to compensate for wear. There are shankless one-piece and two-piece styles. Shankless teeth are basically a cutting face mounted directly onto the saw disk. One- and two-piece designs have a round shank behind the tooth that fits into a bore in the mount. The shank takes some of the loading that would otherwise be carried by the mounting bolt. One-piece teeth are an integral component with tooth and shank, while two-piece teeth have replaceable cutting faces. A one-piece 57 mm kerf long-shank tooth has a mass of nearly 800 g. The more common 51 mm kerf tooth with shank has a mass of about 500 g, while a shankless tooth has a mass of 300 g or less.

The kinetic energy, E_k , of a sawtooth moving at tip speed is calculated in joules as the product of mass and velocity:

$$E_k = 0,5 \times m \times v^2$$

The selection of an appropriate test level for a panel material shall be based on calculation of the anticipated energy level of the potential thrown sawtooth on a particular design. Select a test energy that equals or exceeds the calculated value.

Bibliography

- [1] ISO 8083, *Machinery for forestry — Falling-object protective structures (FOPS) — Laboratory tests and performance requirements*
- [2] ISO 8084, *Machinery for forestry — Operator protective structures — Laboratory tests and performance requirements*
- [3] ISO 11837, *Machinery for forestry — Saw chain shot guarding system — Test method and performance criteria*

British Standards Institution (BSI)

BSI is the independent national body responsible for preparing British Standards and other standards-related publications, information and services.

It presents the UK view on standards in Europe and at the international level.

It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover.

Tel: +44 (0)20 8996 9001 Fax: +44 (0)20 8996 7001

BSI offers Members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Tel: +44 (0)20 8996 7669 Fax: +44 (0)20 8996 7001
Email: plus@bsigroup.com

Buying standards

You may buy PDF and hard copy versions of standards directly using a credit card from the BSI Shop on the website www.bsigroup.com/shop. In addition all orders for BSI, international and foreign standards publications can be addressed to BSI Customer Services.

Tel: +44 (0)20 8996 9001 Fax: +44 (0)20 8996 7001
Email: orders@bsigroup.com

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Knowledge Centre.
Tel: +44 (0)20 8996 7004 Fax: +44 (0)20 8996 7005
Email: knowledgecentre@bsigroup.com

Various BSI electronic information services are also available which give details on all its products and services.

Tel: +44 (0)20 8996 7111 Fax: +44 (0)20 8996 7048
Email: info@bsigroup.com

BSI Subscribing Members are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration.

Tel: +44 (0)20 8996 7002 Fax: +44 (0)20 8996 7001
Email: membership@bsigroup.com

Information regarding online access to British Standards via British Standards Online can be found at www.bsigroup.com/BSOL

Further information about BSI is available on the BSI website at www.bsigroup.com/standards

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies.

Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. This does not preclude the free use, in the course of implementing the standard of necessary details such as

symbols, and size, type or grade designations. If these details are to be used

for any other purpose than implementation then the prior written permission

of BSI must be obtained. Details and advice can be obtained from the Copyright & Licensing Manager.

Tel: +44 (0)20 8996 7070
Email: copyright@bsigroup.com

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Tel +44 (0)20 8996 9001
Fax +44 (0)20 8996 7001
www.bsigroup.com/standards



raising standards worldwide™