

BS ISO 15527:2010



BSI Standards Publication

Plastics — Compression-moulded sheets of polyethylene (PE-UHMW, PE-HD) — Requirements and test methods

NO COPYING WITHOUT BSI PERMISSION EXCEPT AS PERMITTED BY COPYRIGHT LAW

raising standards worldwide™



National foreword

This British Standard is the UK implementation of ISO 15527:2010. It supersedes BS ISO 15527:2007 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee PRI/75, Plastics and rubber film and sheets.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© BSI 2010

ISBN 978 0 580 69424 0

ICS 83.140.10

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 October 2010.

Amendments issued since publication

Date	Text affected
<hr/>	

INTERNATIONAL STANDARD

BS ISO 15527:2010

ISO
15527

Second edition
2010-10-01

Plastics — Compression-moulded sheets of polyethylene (PE-UHMW, PE-HD) — Requirements and test methods

*Plastiques — Plaques moulées par compression en polyéthylène
(PE-UHMW, PE-HD) — Exigences et méthodes d'essai*



Reference number
ISO 15527:2010(E)

© ISO 2010

PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.



COPYRIGHT PROTECTED DOCUMENT

© ISO 2010

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

ii

Contents		Page
Foreword		iv
1	Scope.....	1
2	Normative references.....	1
3	Material.....	1
4	Requirements.....	2
4.1	Appearance.....	2
4.2	Dimensional tolerances	2
4.3	Properties.....	3
5	Test methods	4
5.1	Test specimens.....	4
5.2	Delivery condition	5
5.3	Appearance.....	5
5.4	Dimensions	5
5.5	Density.....	5
5.6	Determination of abrasion properties	5
5.7	Tensile stress at yield, σ_y, and tensile strain at yield, ϵ_y.....	5
5.8	Modulus of elasticity in tension, E_t.....	5
5.9	Impact strength of notched specimens	6
5.10	Melt mass-flow rate (MFR).....	6
6	Designation	6
7	Marking.....	6
Annex A (normative) Requirements for rectangularity.....		7
Annex B (normative) Determination of abrasion properties		8
Annex C (informative) Example of apparatus for the determination of abrasion properties.....		10

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 15527 was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 11, *Products*.

This second edition cancels and replaces the first edition (ISO 15527:2007), of which it constitutes a minor revision (the requirements given in Table 2 for the abrasion properties have been modified and in 5.9.2 ISO 179-1, rather than ISO 11542-2, is now used to determine the Charpy impact strength).

iv

Plastics — Compression-moulded sheets of polyethylene (PE-UHMW, PE-HD) — Requirements and test methods

1 Scope

This International Standard specifies the requirements and test methods for solid flat compression-moulded sheets of polyethylene (PE-UHMW and PE-HD, see ISO 1043-1) without fillers or reinforcing materials. It applies only to thicknesses from 10 mm to 200 mm.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 179-1, *Plastics — Determination of Charpy impact properties — Part 1: Non-instrumented impact test*

ISO 291, *Plastics — Standard atmospheres for conditioning and testing*

ISO 527-2, *Plastics — Determination of tensile properties — Part 2: Test conditions for moulding and extrusion plastics*

ISO 1133, *Plastics — Determination of the melt mass-flow rate (MFR) and the melt volume-flow rate (MVR) of thermoplastics*

ISO 1043-1, *Plastics — Symbols and abbreviated terms — Part 1: Basic polymers and their special characteristics*

ISO 1183 (all parts), *Plastics — Methods for determining the density of non-cellular plastics*

ISO 1872-1, *Plastics — Polyethylene (PE) moulding and extrusion materials — Part 1: Designation system and basis for specifications*

ISO 11542-1, *Plastics — Ultra-high-molecular-weight polyethylene (PE-UHMW) moulding and extrusion materials — Part 1: Designation system and basis for specifications*

ISO 11542-2, *Plastics — Ultra-high-molecular-weight polyethylene (PE-UHMW) moulding and extrusion materials — Part 2: Preparation of test specimens and determination of properties*

3 Material

Sheets shall consist of PE-UHMW moulding materials as defined in ISO 11542-1 or PE-HD selected from polyethylene (PE) moulding materials as defined in ISO 1872-1, without fillers or reinforcing materials. Materials and additives of unknown identity shall not be used.

NOTE Legal conditions may necessitate a specific choice of moulding material (see 4.3.2).

4 Requirements

4.1 Appearance

Sheets shall have smooth surfaces. Small grooves and any resultant irregularities in the thicknesses of sheets are acceptable as long as the requirements specified in 4.2.1 are fulfilled. Sheets shall be examined in accordance with 5.3.

Where agreed between the interested parties, sheets with a smooth machined surface may be supplied.

Sheets shall be substantially free from bubbles, blowholes and other inhomogeneities which would make them unfit for the intended use. Specific requirements with respect to this internal integrity shall be agreed upon between the interested parties. Sheets shall be examined in accordance with 5.2.

4.2 Dimensional tolerances

4.2.1 Thickness

For any individual sheet, the thickness tolerance with reference to the nominal thickness shall be as specified in Table 1. Testing shall be in accordance with 5.4.1.

Table 1 — Tolerances on thickness of sheet

Values in millimetres

Nominal thickness h_n	Tolerance			
	PE-UHMW		PE-HD	
			High MW	Low MW
	Group 1.1	Group 1.2	Group 2.1	Group 3.1
$10 \leq h_n \leq 20$	+3 0	+3 0	+3 0	+3 0
$20 < h_n \leq 40$	+5 0	+5 0	+5 0	+5 0
$40 < h_n \leq 60$	+6 0	+6 0	+6 0	+6 0
$60 < h_n \leq 80$	+8 0	+8 0	+8 0	+8 0
$80 < h_n \leq 100$	+10 0	+10 0	+10 0	+10 0
$100 < h_n \leq 120$	+12 0	+12 0	+12 0	+12 0
$120 < h_n \leq 150$	+14 0	+14 0	+14 0	+14 0
$150 < h_n \leq 200$	+16 0	+16 0	+16 0	+16 0

4.2.2 Length and width

The nominal length, l_n , and nominal width, b_n , of sheets shall be as agreed between the interested parties.

4.2.3 Rectangularity

For any individual sheet, selected at random from any delivery, the rectangularity tolerance, expressed as the difference in length of the diagonals, $|d_1 - d_2|$ (see Figure 1), shall be in accordance with Table A.1.

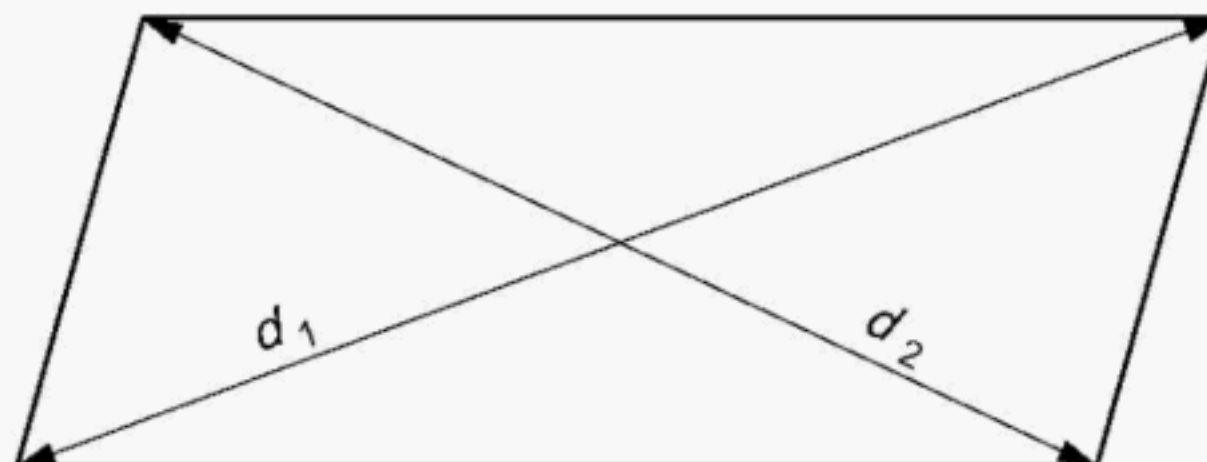


Figure 1 — Difference between lengths of diagonals, $|d_1 - d_2|$

Testing shall be in accordance with 5.4.3.

4.3 Properties

4.3.1 Physical properties

Requirements for physical properties are given in Table 2.

Table 2 — Physical properties

Properties	Unit	Requirements (average values)				Test method subclause
		PE-UHMW		PE-HD		
		Group 1.1	Group 1.2	Group 2.1	Group 3.1	
Density	g/cm ³	0,920 to 0,945	0,920 to 0,945	0,945 to 0,960	0,940 to 0,965	5.5
Abrasion	—	70 to < 90	90 to 110	200 to 450	500 to 1 000	5.6
Tensile stress at yield	MPa	W 17	W 17	W 19	W 19	5.7
Tensile strain at yield	%	W 8	W 8	W 8	W 8	5.7
Modulus of elasticity in tension	MPa	W 500	W 600	W 800	W 700	5.8
Impact strength of double-notched specimens	kJ/m ² 5.9.1	W 40	W 170	W 15	W 5	
Charpy impact strength of notched specimens	kJ/m ²	No breaks	No breaks	No breaks	W 9	5.9.2
MFR: 190 °C/5 kg	g/10 min	Not measurable	Not measurable	u 0,1	0,3 to 0,7	5.10
MFR: 190 °C/21,6 kg	g/10 min	Not measurable	Not measurable	u 3	7 to 20	5.10

4.3.2 Physiological behaviour

Any relevant legislation for physiological behaviour shall be taken into consideration.

5 Test methods

5.1 Test specimens

5.1.1 Preparation of test specimens

For sheets of thickness W 10 mm but \leq 20 mm, the test specimens shall be taken as shown in Figure 2, and for sheets of thickness > 20 mm but \leq 200 mm they shall be taken as shown in Figure 3.

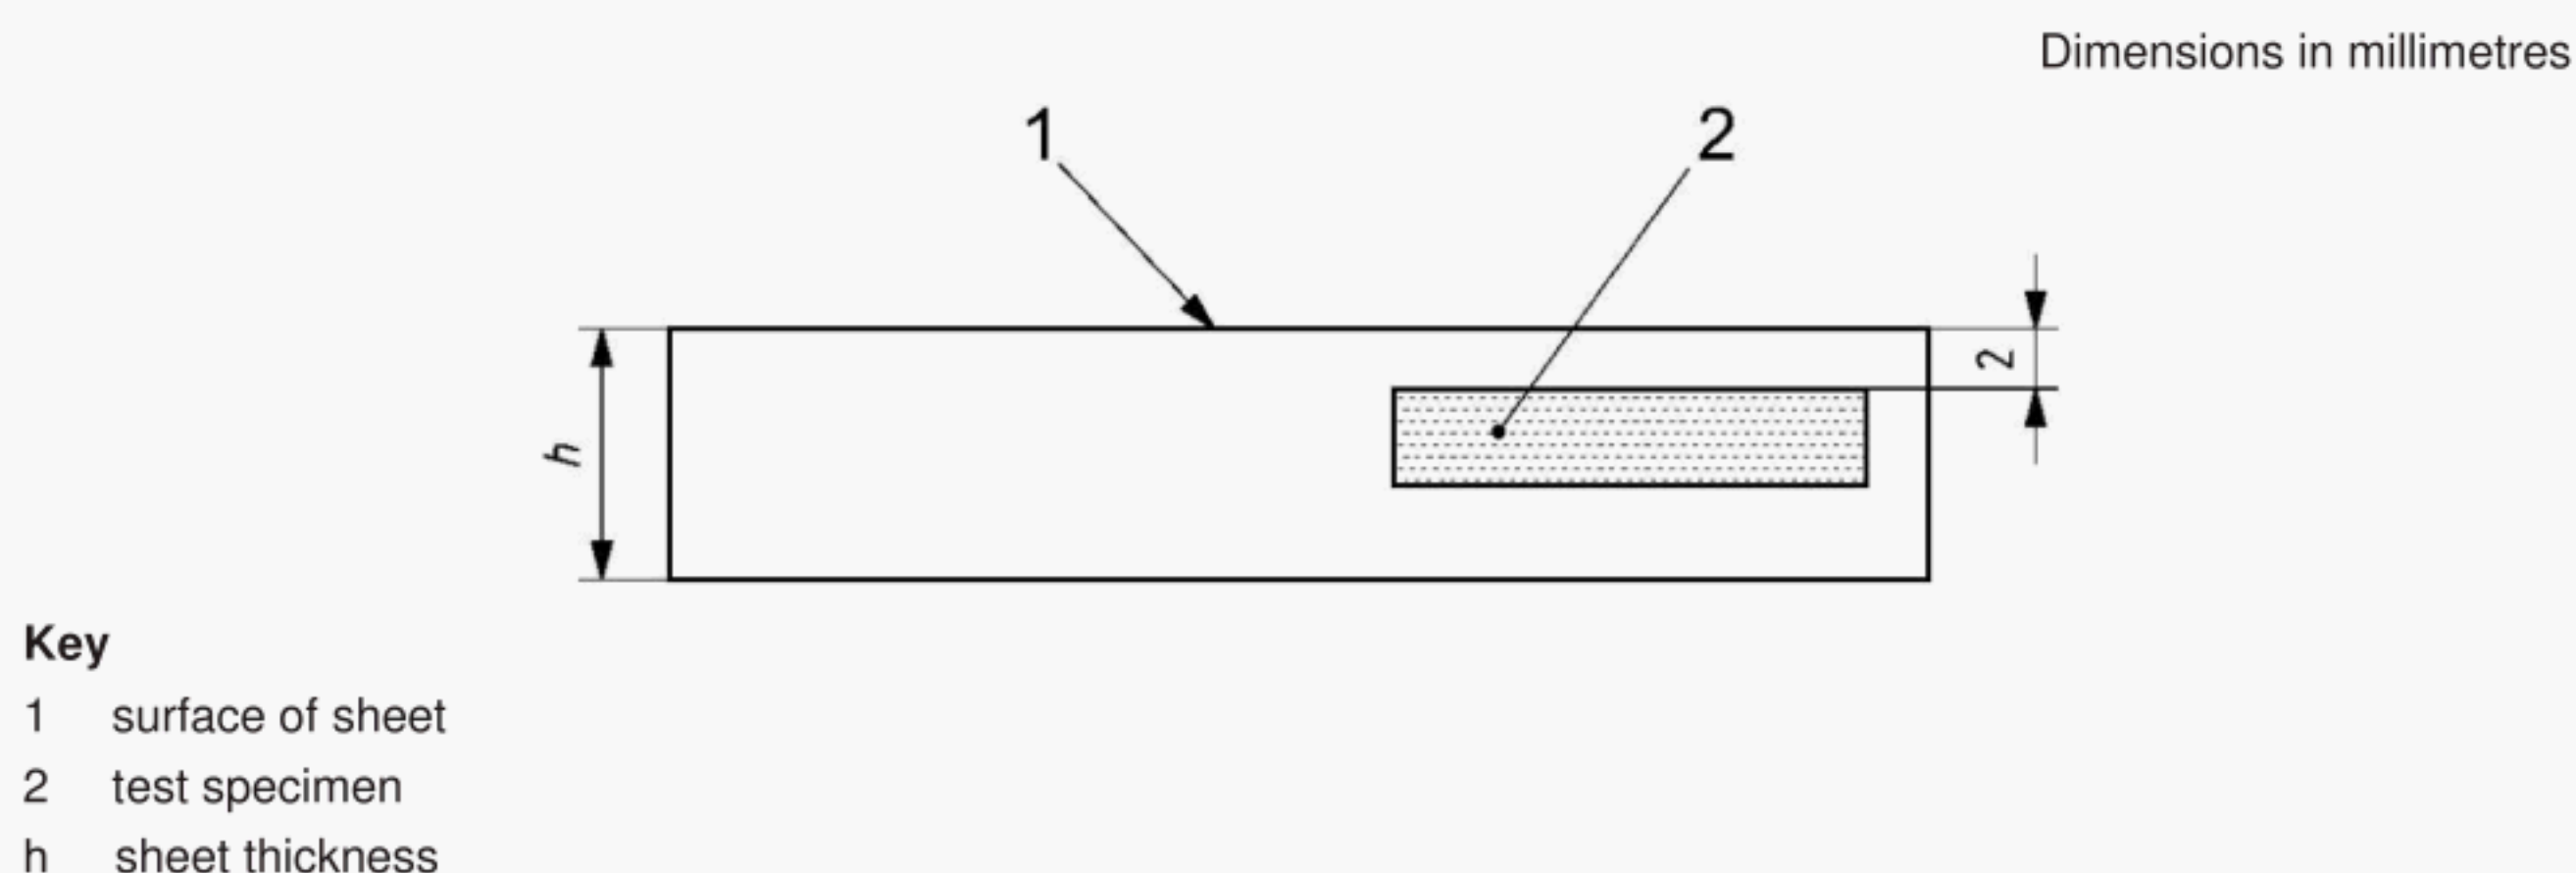


Figure 2 — Taking test specimens from sheets of thickness W 10 mm but \leq 20 mm

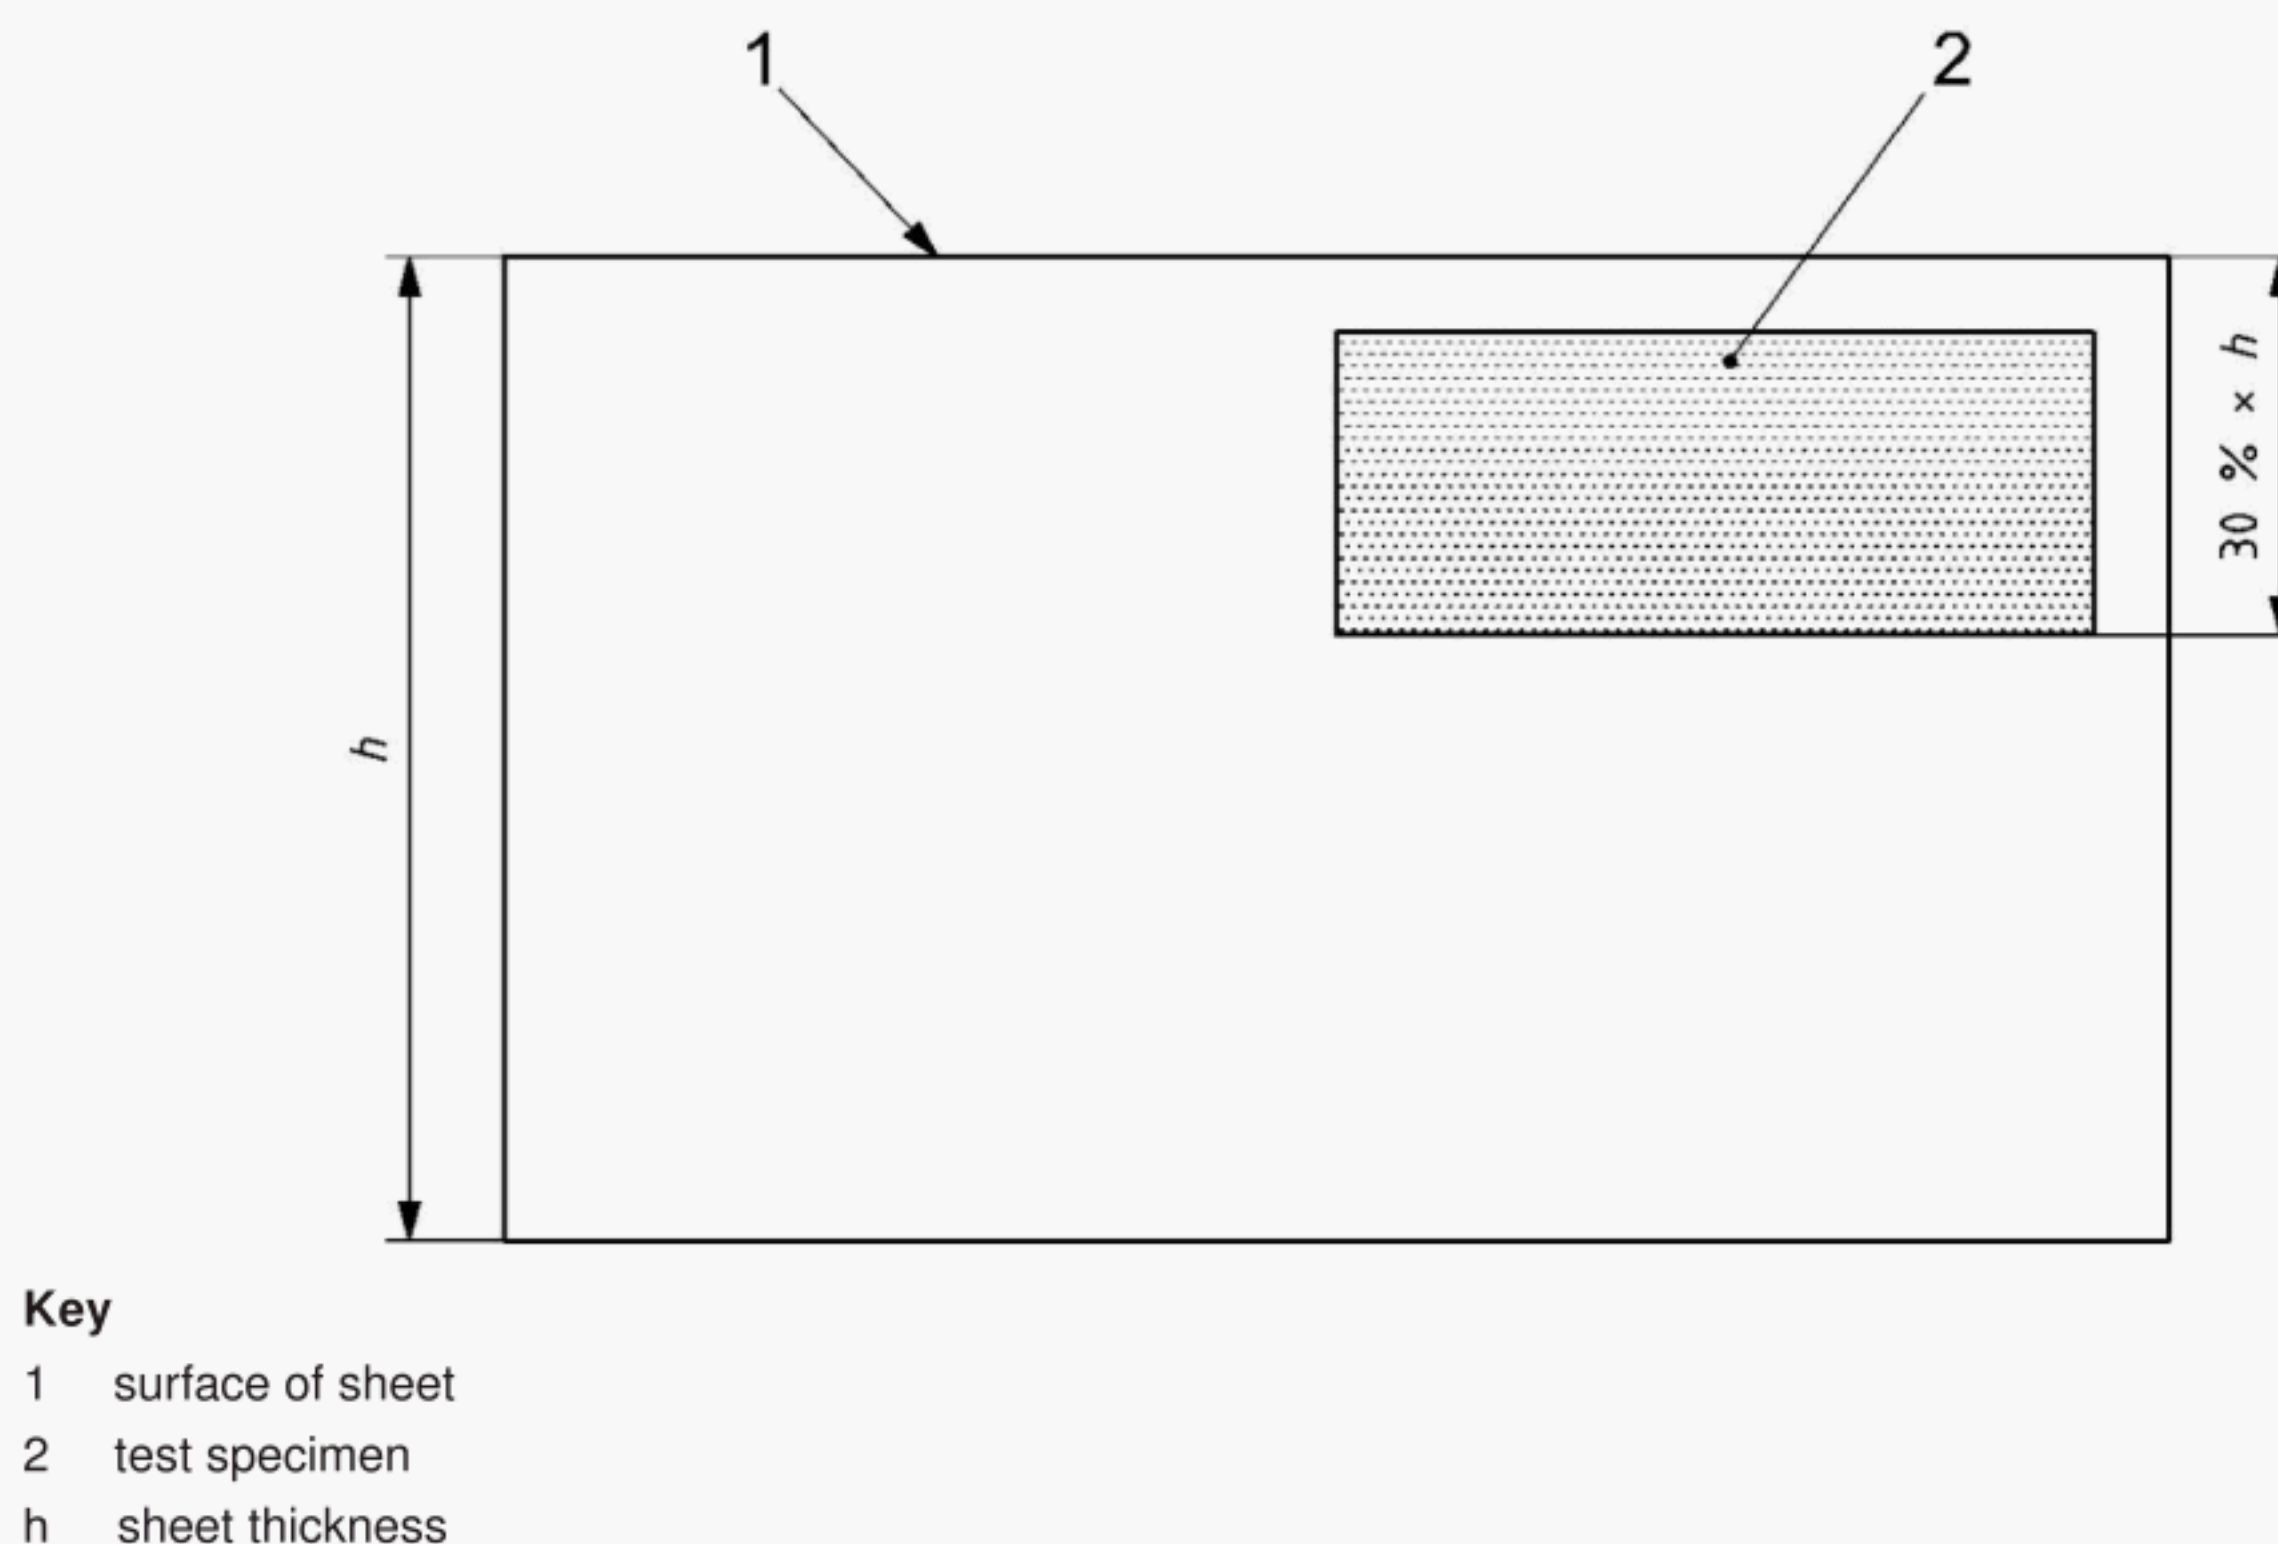


Figure 3 — Taking test specimens from sheets of thickness > 20 mm but \leq 200 mm

The surfaces of the test specimens shall be free from damage and faults in order to avoid notch effects. Should any burrs occur on the test specimens during machining, these shall be eliminated without damaging the surfaces of the specimens. If required, the cut edges shall be finished with abrasive paper (grain size 220 or finer), the direction of abrasion being along the length of the test specimens.

5.1.2 Conditioning

All test specimens shall be conditioned for at least 16 h at $23\text{ °C} \pm 2\text{ °C}$ in accordance with ISO 291 or as specified in the appropriate material standard. Shorter conditioning times may be used by agreement between the interested parties when it can be shown that there is no significant difference in the results obtained.

5.1.3 Testing

Testing shall be carried out in standard atmosphere 23/50 as specified in ISO 291 or as specified in the appropriate material standard, unless otherwise agreed between the interested parties or specified in the individual test standards.

5.2 Delivery condition

Sheets shall be visually examined when delivered to ensure freedom from mechanical damage or other obvious defects. Sheets can be inspected by ultrasonic or X-ray methods where required.

5.3 Appearance

Where possible, sheets shall be examined for visual defects by transmitted light using a suitable light source. Otherwise, sufficiently bright reflected light shall be used. Any defects thus identified shall be compared with the agreed specification (which may be either a written specification or in the form of reference samples) and classified accordingly.

5.4 Dimensions

5.4.1 Thickness, h

The thickness, h , shall be measured using suitable calibrated equipment accurate to $\pm 0,10\text{ mm}$.

5.4.2 Length, l , and width, b

The length, l , and width, b , shall be measured to the nearest 1 mm using suitable equipment. Measurements shall be made directly across the surface of the sheet and along the cut edge.

5.4.3 Rectangularity

The rectangularity, expressed as the difference between the lengths of the diagonals, $|d_1 - d_2|$, as shown in Figure 1, shall be measured to the nearest 1 mm using a graduated ruler or tape measure.

5.5 Density

The density shall be determined in accordance with the appropriate part of ISO 1183.

5.6 Determination of abrasion properties

Preparation of test specimens and abrasion testing shall be carried out in accordance with Annex B.

5.7 Tensile stress at yield, σ_y , and tensile strain at yield, ϵ_y

The tensile stress at yield, σ_y , and tensile strain at yield, ϵ_y , shall be determined using at least five type 1B test specimens in each direction in accordance with ISO 527-2, using a test speed of $50\text{ mm/min} \pm 5\text{ mm/min}$.

5.8 Modulus of elasticity in tension, E_t

The modulus of elasticity in tension, E_t , shall be determined using at least five type 1B test specimens in each direction in accordance with ISO 527-2, using a test speed of $1\text{ mm/min} \pm 0,2\text{ mm/min}$.

5.9 Impact strength of notched specimens

5.9.1 Charpy impact strength of double-notched specimens

The Charpy impact strength of double-notched specimens shall be determined in accordance with ISO 11542-2.

5.9.2 Charpy impact strength of single-notched specimens, a_{cN}

The Charpy impact strength of notched specimens, a_{cN} , shall be determined in accordance with ISO 179-1 (method 1eA), using at least 10 test specimens at $23\text{ }^{\circ}\text{C} \pm 2\text{ }^{\circ}\text{C}$.

5.10 Melt mass-flow rate (MFR)

If appropriate for the material being evaluated, the melt mass-flow rate shall be determined in accordance with ISO 1133 at a temperature of $190\text{ }^{\circ}\text{C}$ and load of 5 kg, and at a temperature of $190\text{ }^{\circ}\text{C}$ and load of 21,6 kg.

6 Designation

Example for PE-UHMW sheets:

	10	sheets	ISO 15527	PE-UHMW-1.1	80 × 2 000 × 1 000	natural
Number of items						
Form in which supplied						
Number of this International Standard						
Material						
Group						
Nominal thickness in millimetres						
Nominal length in millimetres						
Nominal width in millimetres						
Colour						

Designation: 10/sheets/ISO 15527/PE-UHMW-1.1/80 × 2 000 × 1 000/natural

7 Marking

Sheets that conform to this International Standard may be marked with the following information:

- a) the manufacturer's name, trade mark or identification mark;
- b) the number of this International Standard, ISO 15527;
- c) the date of manufacture/batch number.

Annex A (normative)

Requirements for rectangularity

Table A.1 — Maximum limits of deviation from rectangularity (see 4.2.3)

Values in millimetres

Nominal sheet dimensions (length × width)	Maximum limit of deviation from rectangularity $ d_1 - d_2 $
2 000 × 1 000	7
2 000 × 1 500	9
2 000 × 2 000	11
3 000 × 1 000	7
3 000 × 1 500	11
3 000 × 2 000	13
4 000 × 2 000	14
6 000 × 1 000	8
6 000 × 1 500	11


Annex B (normative)

Determination of abrasion properties

B.1 Sampling

Test specimens as shown in Figure B.1 shall be prepared by machining them from the sheet.

Dimensions in millimetres

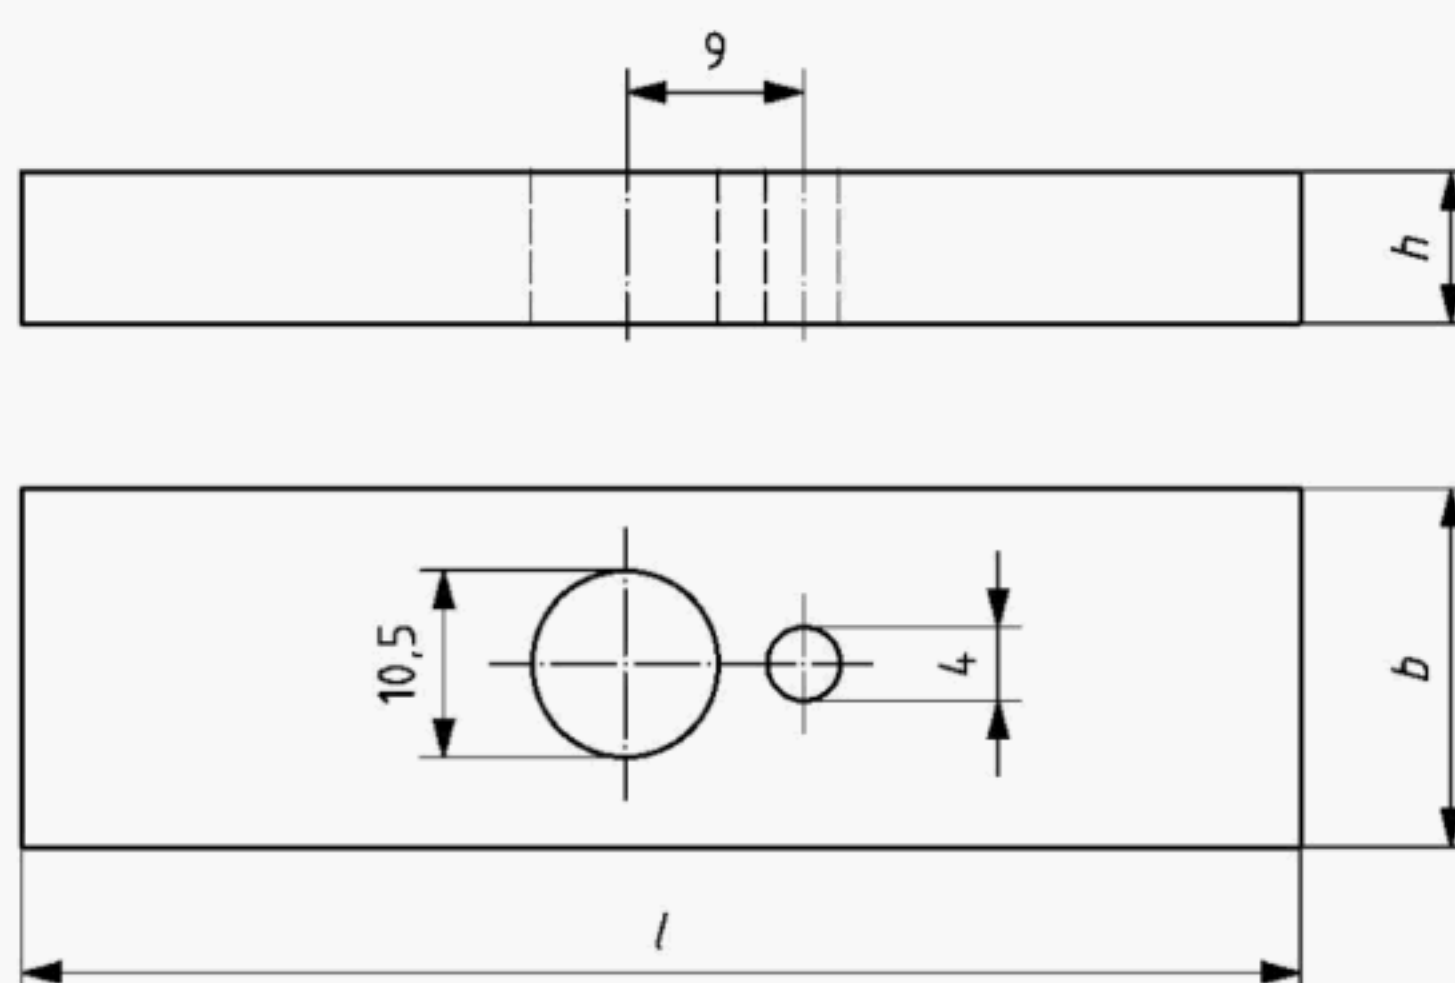

Thickness, h	$6,35 \text{ mm} \pm 0,10 \text{ mm}$
Width, b	$25,40 \text{ mm} \pm 0,20 \text{ mm}$
Length, l	$76,20 \text{ mm} \pm 0,20 \text{ mm}$

Figure B.1 — Machined test specimen

B.2 Testing

Carry out abrasion testing on at least two test specimens. Weigh the specimens before testing. Then, rotate the specimens for at least 3 h in a slurry of abrasive material in water, using an apparatus similar to that shown in Annex C. The rate of rotation shall be $1\,200 \text{ min}^{-1} \pm 200 \text{ min}^{-1}$ and the temperature of the slurry shall not exceed $23 \text{ }^{\circ}\text{C}$.

Use silica sand (grain size 0,2 mm to 1,0 mm) or aluminium oxide (grain size 0,2 mm to 1,0 mm) as the abrasive material. It is recommended that an abrasive/water slurry with a mass ratio of 3:2 be used.

After testing, weigh the test specimens again. The loss in mass of the test specimens shall be at least 50 mg.

For comparable test results, it is necessary to measure a reference specimen during each test. For the abrasion testing of PE-UHMW, a reference specimen made from material with an elongational stress of $0,24 \text{ MPa} \pm 0,01 \text{ MPa}$ and/or a viscosity number of $2\,300 \text{ ml/g} \pm 100 \text{ ml/g}$ (see ISO 11542-1) shall be used.

B.3 Calculation

$$\text{Degree of abrasion} = \frac{\Delta m_s}{\Delta m_r} \times 100$$

where


Δm_s is the change in mass of the test specimen;

Δm_r is the change in mass of the reference specimen.

Annex C (informative)

Example of apparatus for the determination of abrasion properties

The method used for the determination of the abrasion properties is given in Annex B.

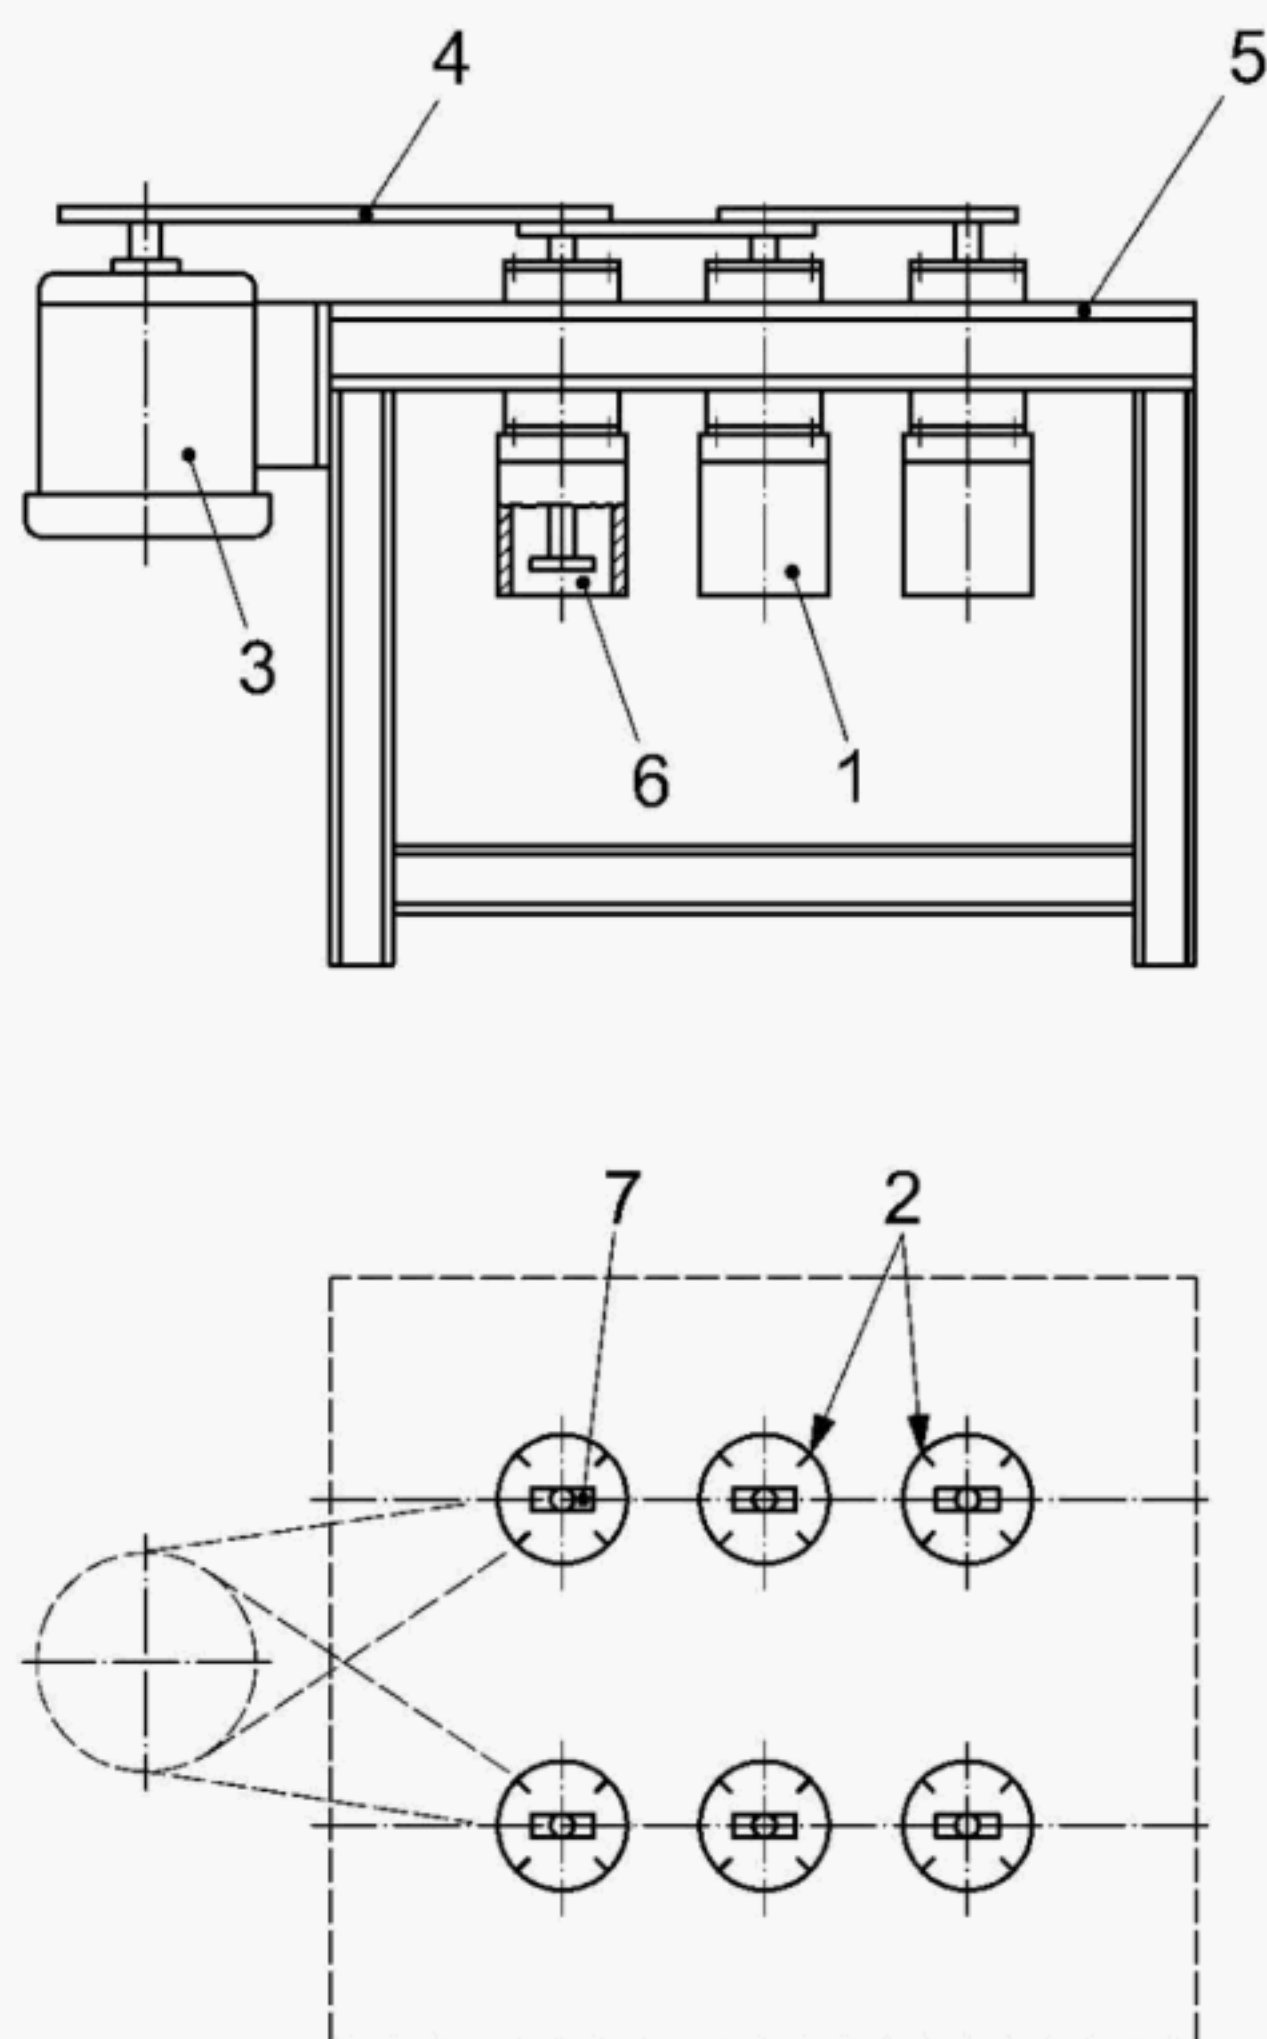

Key

- 1 abrasion test cup (diameter 120 mm, rust-proof steel, with cooling jacket)
- 2 baffles
- 3 drive motor
- 4 belt drive
- 5 supporting structure
- 6 slurry of abrasive in water
- 7 specimen

Figure C.1 — Example of test apparatus

10/10/2020 10:10:10 AM

This page deliberately left blank

British Standards Institution (BSI)

BSI is the independent national body responsible for preparing British Standards and other standards-related publications, information and services.

It presents the UK view on standards in Europe and at the international level.

It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover.

Tel: +44 (0)20 8996 9001 Fax: +44 (0)20 8996 7001

BSI offers Members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Tel: +44 (0)20 8996 7669 Fax: +44 (0)20 8996 7001
Email: plus@bsigroup.com

Buying standards

You may buy PDF and hard copy versions of standards directly using a credit card from the BSI Shop on the website www.bsigroup.com/shop. In addition all orders for BSI, international and foreign standards publications can be addressed to BSI Customer Services.

Tel: +44 (0)20 8996 9001 Fax: +44 (0)20 8996 7001
Email: orders@bsigroup.com

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Knowledge Centre.
Tel: +44 (0)20 8996 7004 Fax: +44 (0)20 8996 7005
Email: knowledgecentre@bsigroup.com

Various BSI electronic information services are also available which give details on all its products and services.

Tel: +44 (0)20 8996 7111 Fax: +44 (0)20 8996 7048
Email: info@bsigroup.com

BSI Subscribing Members are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration.

Tel: +44 (0)20 8996 7002 Fax: +44 (0)20 8996 7001
Email: membership@bsigroup.com

Information regarding online access to British Standards via British Standards Online can be found at www.bsigroup.com/BSOL

Further information about BSI is available on the BSI website at www.bsigroup.com/standards

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies.

Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. This does not preclude the free use, in the course of implementing the standard of necessary details such as

symbols, and size, type or grade designations. If these details are to be used

for any other purpose than implementation then the prior written permission

of BSI must be obtained. Details and advice can be obtained from the Copyright & Licensing Manager.

Tel: +44 (0)20 8996 7070
Email: copyright@bsigroup.com

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Tel +44 (0)20 8996 9001
Fax +44 (0)20 8996 7001
www.bsigroup.com/standards



raising standards worldwide™

Provided by IHS
No reproduction or networking permitted without license from IHS

Not for Resale